

# We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

4,500

Open access books available

118,000

International authors and editors

130M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index  
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?  
Contact [book.department@intechopen.com](mailto:book.department@intechopen.com)

Numbers displayed above are based on latest data collected.  
For more information visit [www.intechopen.com](http://www.intechopen.com)




## The Immobilized Lipases in Biodiesel Production

Margarita Stoytcheva<sup>1</sup>, Gisela Montero<sup>1</sup>,  
Lydia Toscano<sup>1</sup>, Velizar Gochev<sup>2</sup> and Benjamin Valdez<sup>1</sup>  
<sup>1</sup>Universidad Autónoma de Baja California, Instituto de Ingeniería,  
<sup>2</sup>Plovdiv University "Paisii Hilendarski,  
<sup>1</sup>México  
<sup>2</sup>Bulgaria

### 1. Introduction

The leading standard setting organization ASTM International, formerly ASTM (American Society of Testing and Materials), defines biodiesel as a fuel comprised of mono-alkyl esters of long chain fatty acids (ASTM D6751). It is usually manufactured by triglycerides transesterification with methanol or ethanol in the presence of a catalyst, according to the following reaction:

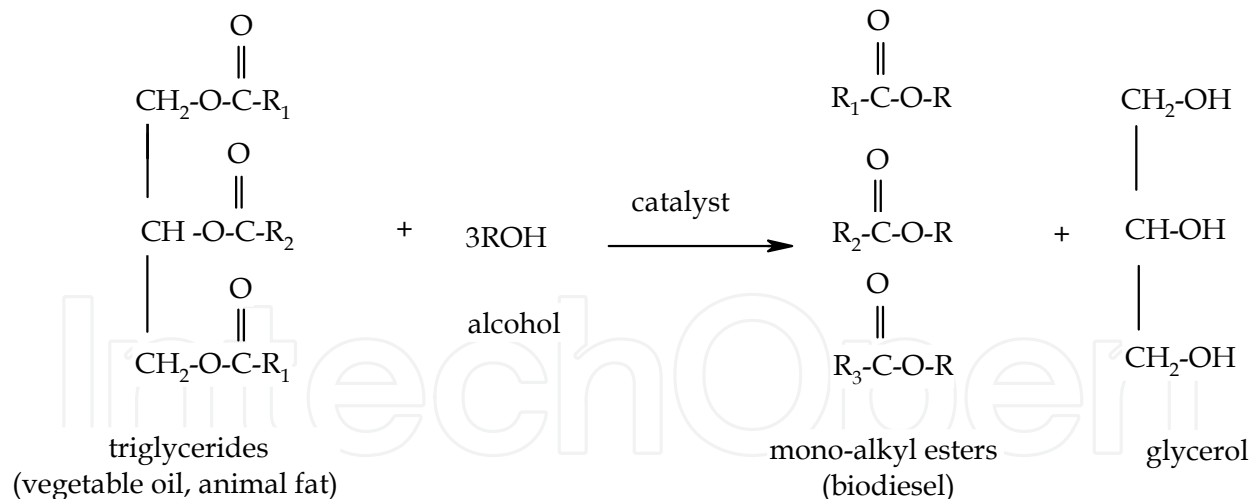


Recently, biodiesel production by lipase catalyzed transesterification has been suggested as a promising alternative to the conventional chemical catalysis, in spite of the high conversion and reaction rates of the latter (Akoh et al., 2007; Bajaj et al., 2010; Bisen et al., 2010; Demirbas, 2009; Fjerbaek et al., 2009; Fukuda et al., 2001, 2009; Ghaly et al., 2010; Helwani et al., 2009; Jegannathan & Abang, 2008; Man Xi Ao et al., 2009; Marchetti et al., 2007; Ranganathan et al., 2008; Robles-Medina et al., 2009; Semwal et al., 2011). The enzymatic process enables eliminating the drawbacks of the alkali- or acid-catalyzed transesterification, namely: product contamination, wastewater release, free fatty acids and water interferences, and difficult glycerol recovery. Nevertheless, the commercialization of

the lipase-catalyzed biodiesel synthesis remains problematic, because of the cost of the enzyme: approximately 1000 USD per kg of Novozym 435 lipase. Therefore, the implementation of strategies, such as enzyme immobilization, for the development of economic and effective enzyme based technologies for biodiesel production is of crucial importance. Enzyme immobilization ensures several issues: repetitive and continuous use of the enzyme and its stabilization, localization of the interaction, prevention of product contamination, reduction of effluent problems and material handling, and effective control of the reaction parameters (D'Souza, 1982). All these aspects are reflected on the production cost.

The present review is intended to provide an overview on the use of immobilized lipases in biodiesel production, the techniques applied for enzyme immobilization, and the factors affecting the process.

## 2. Lipases mode of action and classification

Lipases (EC 3.1.1.3 triacylglycerol acylhydrolase) represent a group of water soluble enzymes that originally catalyze the hydrolysis of ester bonds in water insoluble lipid substrates, acting at the interface between the aqueous and the organic phases. This unique heterogeneous reaction is feasible because of: (i) the specific lipases molecule 3D structure consisting of three domains: "contact domain", responsible for distinguishing of substrate surface, "hydrophobic" domain, responsible for extracting of one substrate molecule and its association with the "functional" domain, and "functional" domain, containing the catalytic triad Ser, Hys and Asp/Glu; (ii) the transition from closed to open conformation in the presence of the lipidic phase (Guncheva & Zhiryakova 2011; Panalotov & Verger, 2000). Enzymatic action of lipases on the substrate is a result of a nucleophilic attack on the carbonyl carbon atom from ester groups. Some lipases are also able to catalyze the processes of esterification, interesterification, transesterification, acidolysis, amynolysis and may show enantioselective properties (Hasan et al., 2009). The mechanism of the lipase catalyzed transesterification of triglycerides with an alcohol to produce biodiesel (Fjerbaek et al., 2009) could be presented by the following sequence of reactions:

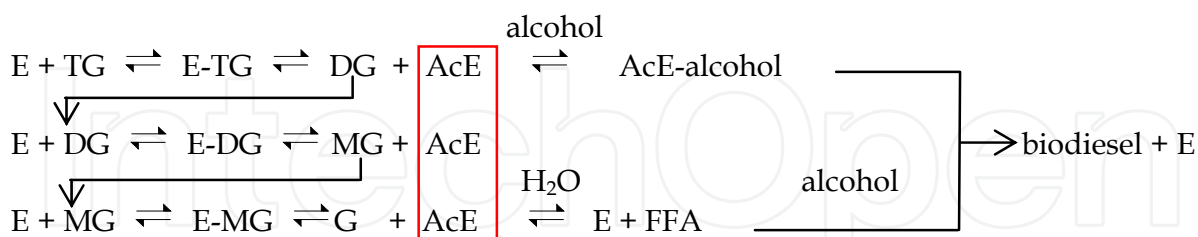


with: E-enzyme; TG-triglyceride; DT-diglyceride; MG-monoglyceride; G-glycerol; AcE-acylated enzyme; FFA-free fatty acid.

According to the origin lipases are plant, animal and microbial. The mostly used lipases in biodiesel production are of bacterial and fungal origin, such as: *Candida antarctica* (Novozym 435), *Candida Rugosa* (Lipase AY), *Pseudomonas cepacia* (Lipase PS), *Pseudomonas fluorescens* (lipase AK), *Pseudomonas aeruginosa*, and *Thermomyces lanuginose* (Lipozime TL), among other. The catalytic properties and potential applications of *Bacillus* lipases are extensively reviewed by Guncheva & Zhiryakova (2011). Among the available lipase producing microorganisms, filamentous fungi belonging to various species of genera *Aspergillus* (Adinarayana et al., 2004; Karanam, & Medicherla, 2008), *Rhizopus* (Hiol et al., 2000; Shukla

& Gupta, 2007), *Penicillium* (Chahinian et al, 2000; Lima et al., 2003; Vardanega et al., 2010), and *Trichoderma* (Kashmiri et al., 2006; Rajesh et al., 2010) are described as the most prospective lipase producers. Only microbial lipases are a matter of practical interest for biodiesel production, because only microbial lipases are produced in industrial scale. The application of the microbial lipases, all together with their immobilization which allows the regeneration and the reuse of the enzyme preparation in several working cycles reduces the production costs, and respectively the final cost of biodiesel. A review on microbial lipase production with emphasis on lipase engineering and use of mathematical models for process improvement and control is provided by Treichel et al. (2010). Some fungi cultured by the authors as powerful producers of lipase of use in biodiesel synthesis are shown in Fig. 1.



*Aspergillus awamori*

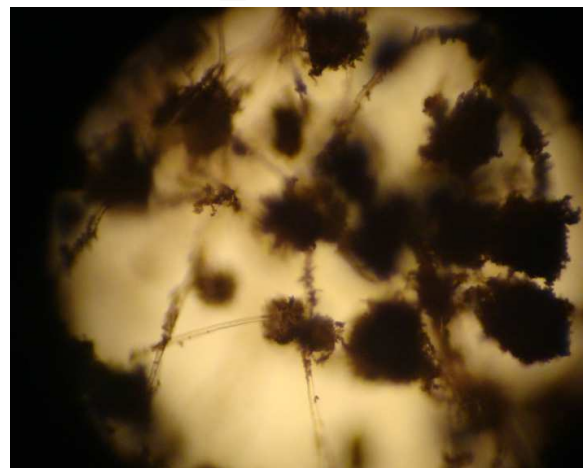

*Aspergillus niger*



*Aspergillus oryzae*



*Penicillium chrysogenum*

Fig. 1. Filamentous fungi belonging to various species of genera *Aspergillus* and *Penicillium*, considered as prospective lipase producers.

### 3. The immobilized lipases in biodiesel production

The term “enzyme immobilization” was defined at the first Enzyme Engineering Conference held at Hennicker, NH, USA, in 1971. It describes “enzymes physically confined at or

localized in a certain region of space with retention of their catalytic activity and which can be used repeatedly and continuously” (Powel, 1996). It is considered that lipase immobilization induces the enzyme conformational change required to enable the free access of substrate to the active centre. Especially, hydrophobic supports allow the adsorption of the open form of the lipases via interfacial activation, mimicking the lipophilic substrate (Ahn et al., 2010; Rodrigues & Fernandez-Lafuente, 2010; Salis et al., 2008; Séverac et al., 2011).

The revision of the literature covering the period 2005-2011 demonstrates that a large variety of matrices have been used for lipases immobilization, and that the main methods applied include adsorption, entrapment and/or encapsulation, and covalent attachment.

### 3.1 Lipases immobilization by adsorption

Physical adsorption is considered as the simplest method for enzyme immobilization. Enzyme fixation is performed through hydrogen bonds, salt linkages, and Van der Waal's forces. The process is carried out in mild conditions, without or with minimum support activation and clean up procedures application, and in the absence of additional reagents. Thus, it is economic and allows preserving enzyme activity and specificity. The chemical composition of the carrier, the molar ratio of hydrophilic to hydrophobic groups, as well as the particle size and the surface area determine the amount of enzyme bound and the enzyme behaviour after immobilization. Some of the most commonly used carriers for lipases immobilization by adsorption are listed in Table 1.

Data shown in Table 1 indicate that among the variety of lipase immobilization supports, Accurel has found a large application. Accurel is the trade name of a group of macroporous polymers. As carriers for lipase immobilization are used the polypropylene based hydrophobic Accurel MP (MP1000 with particle size below 1500 µm, Accurel MP1001 with particle size below 1000 µm and Accurel MP1004 with particle size below 400 µm), and Accurel EP-100. On the most hydrophobic support tested, Accurel MP1001, no glycerol adsorption was observed (Séverac et al., 2011). It has been demonstrated (Salis et al., 2009) comparing the catalytic efficiencies (activity/loading) of eight lipases, that they show a different level of adaptation to the support. Immobilized *Pseudomonas fluorescens* lipase is the most active biocatalyst, followed by immobilized *Pseudomonas cepacia* lipase. The other lipases tested (from *Rhizopus oryzae*, *Candida rugosa*, *Mucor javanicus*, *Penicillium roqueforti*, *Aspergillus niger*, *Penicillium camembertii*), are inactive toward biodiesel synthesis in the described conditions.

Enzyme immobilization on Accurel could be performed by direct contact between the lipase solution and the support (Cheirsilp et al., 2008). However, it has been confirmed that ethanol pre-treatment improves the immobilization process by inducing a better penetration of the enzyme solution inside the hydrophobic Accurel and by reducing the enzyme thermodynamic activity, thus forcing the adsorption process (Foresti, & Ferreira, 2004). Enzyme adsorption with previous ethanol treatment of the support is carried out via: (i) wetting the support with, sequentially: ethanol, aqueous ethanol solution and finally with water, with intermediary filtration, or (ii) a single wetting with ethanol and then a direct contact with the enzyme solution without removing ethanol.

Accurel, due to its hydrophobic properties, should stabilise the enzyme in its open (active) conformation. Thus, it is considered as efficient for lipase immobilization.

Other synthetic polymers used for lipases immobilization comprise: hydrophobic polystyrene macroporous resin (Li & Yan, 2010), electrospun polyacrylonitrile nanofibers



with higher porosity and interconnectivity compared with other nanostructured carriers (Sakai et al., 2010), polymethacrylate (Salis et al., 2009), etc. The naturally occurring materials used as carriers for lipase immobilization include: activated carbon (Moreno-Parajàn & Giraldo, 2011; Naranjo et al., 2010) and carbon cloth (Naranjo et al., 2010), celite (Ji et al., 2010; Shah & Gupta, 2007); hydrotalcite (Yagiz et al., 2007; Zeng et al., 2009), zeolites (Yagiz et al., 2007), etc. The role of the nature of the support surface on the loading and the activity, as well as on the operational stability of the immobilized enzyme has been investigated in details.

Carrier	Immobilized lipase origin	Reference	
Accurel	<i>Candida Antarctica</i>	Séverac et al., 2011; Tongboriboon et al., 2010	
	<i>Candida rugosa</i>	Salis et al., 2008 ; Tongboriboon et al., 2010	
	<i>Pseudomonas cepacia</i>	Salis et al., 2008 ; Tongboriboon et al., 2010	
	<i>Pseudomonas sp.</i>	Cheirsilp et al., 2008	
	<i>Pseudomonas fluorescens</i>	Salis et al., 2008, 2009	
	<i>Pseudomonas fluorescens</i>	Tongboriboon et al., 2010	
	<i>Mucor javanicus</i>	Salis et al., 2008	
	<i>Penicillium roqueforti</i>	Salis et al., 2008	
	<i>Penicillium camembertii</i>	Salis et al., 2008	
	<i>Rhizopus oryzae</i>	Salis et al., 2008	
Activated carbon	<i>Thermomyces lanuginosus</i>	Tongboriboon et al., 2010	
	<i>Candida Antarctica</i>	Naranjo et al., 2010	
	<i>Candida rugosa</i>	Moreno-Parajàn & Giraldo, 2011	
	Celite	<i>Candida rugosa</i>	Shah & Gupta, 2007
		<i>Pseudomonas cepacia</i>	Shah & Gupta, 2007
		<i>Pseudomonas aeruginosa</i>	Ji et al., 2010
		<i>Pseudomonas fluorescens</i>	Shah & Gupta, 2007
	Polystyrene	<i>Pseudomonas cepacia</i>	Li & Yan, 2010
	Carbon cloth	<i>Pseudomonas cepacia</i>	23 Naranjo et al., 2010
	Poly(acrylonitrile)	<i>Pseudomonas cepacia</i>	16 Sakai et al., 2010
Ceramics	<i>Pseudomonas cepacia</i>	Shah & Gupta, 2007	
Pre-treated textile	<i>Candida sp.</i>	Chen et al., 2009; Li et al., 2010 ; Lu et al., 2007 and 2010	
	Hydrophilic resins	<i>Rhizomucor miehei</i>	De Paola et al., 2009
<i>Rhizomucor miehei</i>		Chen et al., 2009	
<i>Pseudomonas fluorescens</i>		Salis et al., 2009	
Mg-Al hydrotalcites	<i>Saccharomyces cerevisiae</i>	Zeng et al., 2009	
Resin D4020	<i>Penicillium expansum</i>	Li et al., 2009	
Polymethacrylate	<i>Pseudomonas fluorescens</i>	Salis et al., 2009	
Organosilicate	<i>Pseudomonas fluorescens</i>	Salis et al., 2009	
Hydrotalcite	<i>Thermomyces lanuginosus</i>	Yagiz et al., 2007	
Zeolites	<i>Thermomyces lanuginosus</i>	Yagiz et al., 2007	

Table 1. Carrier used for lipases immobilization by adsorption.

### 3.2 Lipases immobilization by entrapment and/or encapsulation

Entrapment involves capture of the enzyme within a matrix of a polymer, although enzyme encapsulation refers to the formation of a membrane-like physical barrier around the enzyme preparation (Cao, 2005). The matrix is usually formed during the process of the immobilization. The enzyme entrapped in a gel matrix can be further encapsulated. Both processes require simple equipment and relatively inexpensive reagents. It is supposed that

enzymes immobilized by entrapment and/or encapsulation are more stable than the physically adsorbed ones. At the same time the immobilized enzymes maintain their activity and stability.

Numerous materials and techniques have been used for lipases entrapment and/or encapsulation. Some of the immobilization matrices developed during the last years (2005-2011) are enumerated in Table 2.

Carrier	Immobilized lipase origin	References
κ-carrageenan	<i>Candida Antarctica</i>	Jegannathan et al., 2010
	<i>Candida rugosa</i>	Jegannathan et al., 2010
	<i>Burkholderia cepacia</i>	Jegannathan et al., 2009, 2010
	<i>Pseudomonas fluorescens</i>	Jegannathan et al., 2010
	<i>Aspergillus niger</i>	Jegannathan et al., 2010
Silica gel	<i>Thermomyces lanuginosus</i>	Khor et al., 2010
	<i>R. miehei</i>	Macario et al., 2009
	<i>Pseudomonas cepacia</i>	Noureddini et al., 2005
Celite supported sol-gel	<i>Candida Antarctica</i>	Meunier & Legge, 2010
	Lipase NS44035	Meunier & Legge, 2010
Silica aerogel	<i>Candida Antarctica</i>	Nassreddine et al., 2008
	<i>Candida Antarctica</i>	Orçaire et al., 2006
	<i>Burkholderia cepacia</i>	Orçaire et al., 2006

Table 2. Carrier used for lipases immobilization by entrapment and/or encapsulation.

For instance, a simple technique for lipase encapsulation in κ-carrageenan by co-extrusion was suggested by Jegannathan et al. (2009, 2010). Carrageenan has been selected because of its availability, biodegradability, low cost, and lack of toxicity. It was found that at optimized reaction conditions a methyl ester conversion up to 100% could be achieved in transesterification of palm oil using the liquid core encapsulated lipase PS from *Burkholderia cepacia*. The immobilized lipase was stable and retained 82% relative transesterification activity after five cycles.

Another technique for lipase immobilization by entrapment and/or encapsulation, which has received a considerable attention in recent years, is the sol-gel process. The method involves an aqueous solution of the enzyme, a catalyst (NaOH, NaF, HCl), and an inorganic-organic matrix precursor (alkoxysilane). The hydrolysis and condensation of the precursor result in an amorphous silica matrix that covers the enzyme. The method has been applied for *R. miehei* lipase encapsulation within the micellar phase of a surfactant that is self-assembled with silica (Macario et al., 2009). It has been demonstrated that the enzyme preserves its mobility and activity. More over, because of the activation of the enzyme catalytic centre by the hydrophobic groups of the surfactant, the immobilized lipase was more active than its free form. In addition, the obtained ordered mesoporous structure improved the stability of the enzyme and decreased the rate of leaching.

Comprehensive characterization of sol-gel immobilized lipase has been performed by Noureddini et al. (2005). Lipase PS was entrapped within a sol-gel polymer matrix, prepared by polycondensation of hydrolyzed tetramethoxysilane and isobutyltrimethoxysilane. The immobilized lipase was stable and more active than the free lipase toward the transesterification of soybean oil.

Various supports could be used to improve the stability of the entrapped/encapsulated enzymes. Celite supported lipase sol-gels were investigated aiming such problems as

activity, stability and reusability of the enzyme (Meunier & Legge, 2010). The three types of Celite considered (R633, R632, and R647) were compared to unsupported lipase sol-gels. It has been established that sol-gel immobilized lipase supported on Celite R632 allowed achieving an average conversion of 60% per gram of material for 6 h, and exhibited an average initial lipase activity comparable to that of the unsupported sol-gel formulation.

Orçaire et al. (2006) report a technique for encapsulation of *Candida Antarctica* and *Burkholderia cepacia* lipases in silica aerogels reinforced with silica quartz fibre felt and dried by the CO<sub>2</sub> supercritical technique. The aerogel encapsulation permits maintaining the enzymes in a dispersion state similar to the dispersion prevailing in an aqueous solution, even in organic media, while agglomeration of the lipase occurs if it is used directly in the organic solvent. At present, sol-gel enzyme entrapment/encapsulation is considered to be the most successful immobilization technique for lipase immobilization.

### 3.3 Lipases immobilization by covalent attachment

Covalent attachment is a result of a chemical reaction between the active amino acid residues outside the active catalytic and binding site of the enzyme, and the active functionalities of the carrier (Cao, 2005). Although drastic and complicated, and strongly affected by the carriers' properties, covalent attachment is the most efficient technique for enzyme immobilization. Some carriers used for covalent lipase immobilization are displayed in Table 3.

Carrier	Immobilized lipase origin	References
Olive pomace	<i>Thermomyces lanuginosus</i>	Yücel, 2011
Resins	<i>Thermomyces lanuginosus</i>	Mendes et al., 2011
	<i>Pseudomonas fluorescens</i>	Mendes et al., 2011
Polymers	<i>Thermomyces lanuginosus</i>	Dizge et al., 2008, 2009a, 2009b
Polyurethane foam	<i>Thermomyces lanuginosus</i>	Dizge & Keskinler, 2008
Nb <sub>2</sub> O <sub>5</sub> and SiO <sub>2</sub> -PVA	<i>Burkholderia cepacia</i>	Da Rys et al., 2010
Chitosan	<i>Candida rugosa</i>	Shao et al., 2008
		Ting et al., 2008
Lewatit	<i>Thermomyces lanuginosus</i>	Rodrigues et al., 2010
Silica	<i>Rhizopus oryzae</i> + <i>Candida rugosa</i>	Lee and al., 2008
	<i>Enterobacter aerogenes</i>	Kumari et al., 2009
Magnetic nanostructures	<i>Candida rugosa</i>	Dussan et al., 2007, 2010
	<i>Thermomyces lanuginosus</i>	Xie & Ma, 2010

Table 3. Carrier used for lipases immobilization by covalent attachment

Yücel (2011) reports a method for *Thermomyces lanuginosus* lipase covalent binding on polyglutaraldehyde-activated olive pomace powder. The technique is cost effective, because of the low price of the support and because of the strong covalent bond formed, leading to enzyme stabilization without loss of activity, allowing the multiple reuse of the enzyme. Immobilized lipase was stable for 10 batches of pomace oil transesterification retaining more than 80% residual activity.

Among the other naturally occurring materials, chitosan is considered as appropriate for enzyme binding. Its membrane forming and adhesion ability, high mechanical strength and facility of forming insoluble in water thermally and chemically inert films make it suitable for lipase immobilization. For instance, *Candida rugosa* type VII lipase was fixed onto chitosan beads using a binary method consisting in the follows: (i) lipase



immobilization onto the hydroxyl groups of chitosan by activation with 1-ethyl-3-(3-dimethylaminopropyl) carbodiimide hydrochloride; (ii) immobilization of additional lipase molecules through their amino groups to chitosan by cross-linking with glutaraldehyde. The immobilized enzyme has been used to catalyse the hydrolysis of soybean oil. Then, the feedstock containing free fatty acids, mono-, di- and triglycerides was esterified with methanol in the presence of an acid catalyst to produce biodiesel. It has been demonstrated that the enzymatic/acid-catalyzed hybrid process uses milder reaction conditions and allows avoiding the inactivation of the immobilized enzyme by polar compounds and increase biodiesel yields.

A new method for the synthesis of hydrophobic microporous matrices for enzyme immobilization, namely styrene-divinylbenzene-polyglutaraldehyde and poly(styrene-divinylbenzene)-polyglutaraldehyde copolymers, applying High Internal Phase Emulsions (HIPE) technique has been developed by Dizge et al. (2008, 2009a, 2009b). *Thermomyces lanuginosus* lipase was successfully attached to the support by covalent binding. According to the authors, the copolymers could be prepared in a short time and in large amounts and shapes. The immobilization efficiency, defined as the ratio of the activity of the immobilized enzyme to the activity of the free enzyme was found to vary from 80% to 89%. The immobilized enzyme retained its activity during 10-15 repeated batch reactions.

Promising results in terms of enzyme thermal and operational stability improvement have been obtained using as supports for lipases immobilization silanized Nb<sub>2</sub>O<sub>5</sub> and SiO<sub>2</sub>-PVA (Da Rys et al., 2010), and glutaraldehyde or ethanolamine activated silica gels (Lee and al., 2008; Kumari et al., 2009). However, the stability of the immobilized enzyme depends not only on the chemical/physical nature of the carrier, but also on the binding mode, the binding number, and the position of the binding on the enzyme surface (Cao, 2005), among other. Mendes et al. (2011) and Rodrigues et al. (2010) demonstrate that the multipoint covalent attachment of *Thermomyces lanuginosus* lipase on Toyopearl AF-amino-650M resin and on aldehyde-Lewatit is an efficient strategy for enzyme stabilization. It has been demonstrated that *Thermomyces lanuginosus* lipase immobilized on glyoxyl-resin is between 27 and 31 times more stable than the soluble lipase (Mendes et al., 2011).

Another important issue provided by enzyme immobilization concerns the localization of the interaction in the zone where the maximum concentration of reagents is present and/or at the interface between the immiscible heterogeneous phases, regarding lipases. For this purpose, lipases (from *Candida rugosa* and *Thermomyces lanuginosus*) have been immobilized on magnetic nanostructures (Fe<sub>3</sub>O<sub>4</sub>) and localized by application of a magnetic field. In addition, the method favours the simple and fast separation of the enzyme from the reaction mixture. Thus, it allows the intensification of the process and the reduction of the production costs.

### 3.4 Cells immobilization

The technological and economic advantages of immobilized cells over immobilized enzymes are well known (D'Souza, 1982): higher operational stability, higher yields of enzyme activity after immobilization, greater resistance to environmental perturbations, greater potential for multistep processes, and lower effective enzyme cost (enzyme purification and extraction are avoided). Despite of these benefits, only few investigations on the use of immobilized cells in biodiesel synthesis are reported until now (Fukuda et al., 2009; Hama et al., 2006, 2007; Li et al., 2007; Oda et al., 2005; Tamalampudi et al., 2008). The research efforts were focused on the immobilization no more than of *Rhizopus oryzae* within porous biomass

support particles. The fixation was achieved spontaneously during batch cultivation. The applied technique (Atkinson et al., 1979) offers numerous advantages over other methods: the particles are reusable and mechanically resistant; additional reagents, aseptic handling of particles, and preproduction of cells are not necessary. It has been demonstrated that *Rhizopus oryzae* cells immobilized within biomass support particles can be used as low cost catalyst for biodiesel production.

#### 4. Conclusion

Enzymatic approach to biodiesel production offers several advantages over the chemical catalysis currently applied. It is more efficient because of the enzyme specificity and selectivity, involves less energy consumption because of the mild reaction conditions, and is environmentally friendly because of the limited release of side products or wastes. Catalyst immobilization presents a number of additional benefits, such as repeated use of the enzymes, enhancement of their thermal and operational stability, localization of the interaction, effective control of the reaction parameters, etc., thus reducing the production cost and making the enzyme biodiesel synthesis an attractive alternative to other technologies. The present review provides an overview on the techniques applied for lipases immobilization.

#### 5. References

- Adinarayana, K.; Bapi Raju, K. V. V. S. N.; Zargar, M. I. ; Devi, R. B.; Lakshmi, P. J. & Ellaiah, P. (2004). Optimization of process parameters for production of lipase in solid-state fermentation by newly isolated *Aspergillus* species, *Ind. J. Biotechnol.*, 3, 65-69
- Ahn, K.; Ye, S.; Chun, W.; Rah, H. & Kim, S. (2010). Yield and component distribution of biodiesel by methanolysis of soybean oil with lipase-immobilized mesoporous silica. *Microporous and Mesoporous Materials* doi:10.1016/j.micromeso.2010.11.008 (in press)
- Akoh, C.; Chang, Shu-Wei; Lee, Guan-Chiun & Shaw, Jei-Fu (2007). Enzymatic approach to biodiesel production. *J. Agric. Food Chem.* 55, 8995-9005
- ASTM D6751: American Society for Testing and Materials standard specification for biodiesel fuel (B 100) blend stock for distillate fuels
- Atkinson, B.; Black, G. M.; Lewis, P. J. S. & Pinches, A. (1979). Biological particles of given size, shape, and density for use in biological reactors. *Biotechnol. Bioeng.*, 21, 193-200
- Bajaj, A.; Lohan, P.; Jha, P. & Mehrotra, R. (2010). Biodiesel production through lipase catalyzed transesterification: An overview. *J. Mol. Catal. B: Enzymatic*, 62, 9-14
- Bisen, P.; Sanodiya, B.; Thakur, G.; Baghel, R. & Prasad, G. B. K. S. (2010). Biodiesel production with special emphasis on lipase-catalyzed transesterification. *Biotechnol. Lett.*, 32, 1019-1030
- Cao, L. (2005). *Carrier-bound immobilized enzymes. Principles, application and design*. Wiley-VCH, ISBN-10: 3-527-31232-3, Weinheim
- Chahinian, H.; Vanot, G.; Ibrik, A.; Rugani, N.; Sarda, L. & Comeau, L. C. (2000). Production of extracellular lipases by *Penicillium cyclopium* purification and characterization of a partial acylglycerol lipase. *Biosci. Biotechnol. Biochem.*, 64, 215-222

- Cheirsilp, B.; H-Kittikuna, A. & Limkatanyu, S. (2008). Impact of transesterification mechanisms on the kinetic modeling of biodiesel production by immobilized lipase. *Biochem. Eng. J.*, 42, 261–269
- Chen, Y.; Xiao, B.; Chang, J.; Fu, Y.; Lv, P. & Wang, X. (2009). Synthesis of biodiesel from waste cooking oil using immobilized lipase in fixed bed reactor. *Energy Conversion and Management*, 50, 668–673
- Da Rys, P.; Silva, G.; Mendes, A.; Santos, J. & Castro, H. (2010). Evaluation of the catalytic properties of *Burkholderia cepacia* lipase immobilized on non-commercial matrices to be used in biodiesel synthesis from different feedstocks. *Bioresource Technology*, 101, 5508–5516
- De Paola, M. G.; Ricca, E.; Calabrò, V.; Curcio, S. & Iorio, G. (2009). Factor analysis of transesterification reaction of waste oil for biodiesel production. *Bioresource Technology*, 100, 5126–513
- Demirbas, A. (2009). Progress and recent trends in biodiesel fuels. *Energy Conversion and Management*, 50, 14–34
- Dizge, N. & Keskinler, B. (2008). Enzymatic production of biodiesel from canola oil using immobilized lipase. *Biomass and Bioenergy*, 32, 1274–1278
- Dizge, N.; Keskinler, B. & Tanriseven, A. (2008). Covalent attachment of microbial lipase onto microporous styrene-divinylbenzene copolymer by means of poly glutaraldehyde. *Colloids and Surfaces B: Biointerfaces*, 66, 34–38
- Dizge, N.; Keskinler, B. & Tanriseven, A. (2009a). Biodiesel production from canola oil by using lipase immobilized onto hydrophobic microporous styrene-divinylbenzene copolymer. *Biochem. Eng. J.*, 44, 220–225
- Dizge, N.; Aydinler, C.; Imer, D.; Bayramoglu, M.; Tanriseven, A. & Keskinler, B. (2009b). Biodiesel production from sunflower, soybean, and waste cooking oils by transesterification using lipase immobilized onto a novel microporous polymer. *Bioresource Technology*, 100, 1983–1991
- D'Souza, S. F. (1989). Immobilized cells: techniques and applications. *Indian J. Microbiol.*, 29, 83–117
- Dussán, K.; Giraldo, O. & Cardona, C. (2007). Application of magnetic nanostructures in biotechnological processes: Biodiesel production using lipase immobilized on magnetic carriers. *Proceedings of European Congress of Chemical Engineering (ECCE-6)*, Copenhagen, 16–20 September 2007
- Dussan, K.; Cardona, C.; Giraldo, O.; Gutiérrez, L. & Pérez, V. (2010). Analysis of a reactive extraction process for biodiesel production using a lipase immobilized on magnetic nanostructures. *Bioresource Technology*, 101, 9542–9549
- Fjerbaek, L.; Christensen, K. & Norddahl, B. (2009). A Review of the Current State of Biodiesel Production Using Enzymatic Transesterification. *Biotechnol Bioeng.*, 102, 5, 1298–1315
- Foresti, M. L. & Ferreira M. L. (2004). Ethanol pretreatment effect and particle diameter issues on the adsorption of *Candida rugosa* lipase onto polypropylene powder. *Appl. Surf. Sci.*, 238, 86–90
- Fukuda, H.; Kondo, A. & Noda, H. (2001). Biodiesel fuel production by transesterification of oils. *J. Bioscience Bioeng.*, 5, 405–416
- Fukuda, H.; Kondo, A. & Tamalampudi, S. (2009). Bioenergy: Sustainable fuels from biomass by yeast and fungal whole-cell biocatalysts. *Biochem. Eng. J.*, 44, 2–12

- Ghaly, A. E.; Dave, D.; Brooks, M. S. & Budge, S. (2010). Production of biodiesel by enzymatic transesterification: Review. *Am. J. Biochem. Biotechnol.*, 6, 54-76
- Guncheva, M. & Zhiryakova, D. (2011). Catalytic properties and potential applications of *Bacillus* lipases. *J. Mol. Catalysis B: Enzymatic*, 68, 1-21
- Hama, S.; Tamalampudi, S.; Fukumizu, T.; Miura, K.; Yamaji, H.; Kondo, A. & Fukuda, H. (2006). Lipase localization in *Rhizopus oryzae* cells immobilized within biomass support particles for use as whole-cell biocatalysts in biodiesel-fuel production. *J. Bioscience Bioeng.*, 101, 328-333
- Hama, S.; Yamaji, H.; Fukumizu, T.; Numata, T.; Tamalampudi, S.; Kondo, A. Noda, H. & Fukuda, H. (2007). Biodiesel-fuel production in a packed-bed reactor using lipase-producing *Rhizopus oryzae* cells immobilized within biomass support particles. *Biochem. Eng. J.*, 34, 273-278
- Hasan, F.; Shah, A. & Hameed, A. (2009). Methods for detection and characterization of lipases: A comprehensive review. *Biotechnol. Adv.*, 27, 782-798
- Helwani, Z.; Othman, M. R.; Aziz, N.; Fernando, W. J. N. & Kim, J. (2009). Technologies for production of biodiesel focusing on green catalytic techniques: A review. *Fuel Processing Technology*, 90, 1502-1514
- Hiol, A.; Jonzo, M. D.; Rugani, N.; Druet, D.; Sarda, L. & Comeau, L. C. (2000). Purification and characterization of an extracellular lipase from a thermophilic *Rhizopus oryzae* strain isolated from palm fruit. *Enzyme Microb. Technol.*, 26, 421-30
- Jegannathan, K.; Jun-Yee, L.; Chan, E. & Ravindra, P. (2009). Design an immobilized lipase enzyme for biodiesel production. *J. Renewable and Sustainable Energy*, 1, 063101-1 - 063101-8
- Jegannathan K. Abang, S. (2008). Production of biodiesel using immobilized lipase-A critical review. *Critical Reviews in Biotechnology*, 28, 253-264
- Jegannathan, K.; Jun-Yee, L.; Chan, E. & Ravindra, P. (2010). Production of biodiesel from palm oil using liquid core lipase encapsulated in  $\kappa$ -carrageenan. *Fuel*, 89, 2272-2277
- Ji, Q.; Xiao, S.; He, B. & Liu, X. (2010). Purification and characterization of an organic solvent-tolerant lipase from *Pseudomonas aeruginosa* LX1 and its application for biodiesel production. *J. Mol. Catal. B: Enzymatic*, 66, 264-269
- Karanam, S. K. & Medicherla, N. R. (2008). Enhanced lipase production by mutation induced *Aspergillus japonicus*. *African J. Biotechnol.*, 7, 2064-2067
- Kashmiri, M. A.; Adnan, A.; Butt, B. W. (2006). Production, purification and partial characterization of lipase from *Trichoderma viride*. *African J. Biotechnol.*, 5, 878-882
- Khor, G.; Sim, J.; Kamaruddin, A. & Uzir, M. (2010). Thermodynamics and inhibition studies of lipozyme TL IM in biodiesel production via enzymatic transesterification. *Bioresource Technology*, 101, 6558-6561
- Kumari, A.; Mahapatra, P.; Garlapati, V. & Banerjee, R. (2009). Enzymatic transesterification of *Jatropha* oil. *Biotechnology for Biofuels*, 2:1, doi:10.1186/1754-6834-2-1
- Lee Jong Ho; Dong Hwan Lee; Jung Soo Lim; Byung-Hwan Um; Chulhwan Park; Seong Woo Kang & Seung Wook Kim (2008). Optimization of the process for biodiesel production using a mixture of immobilized *Rhizopus oryzae* and *Candida rugosa* lipases. *J. Microbiol. Biotechnol.*, 18, 1927-1931
- Li, N.; Zong, M.; Wu, H. (2009). Highly efficient transformation of waste oil to biodiesel by immobilized lipase from *Penicillium expansum*. *Process Biochemistry*, 44, 685-688



- Li, Q. & Yan, Y. (2010). Production of biodiesel catalyzed by immobilized *Pseudomonas cepacia* lipase from *Sapium sebiferum* oil in micro-aqueous phase. *Applied Energy*, 87, 3148–3154
- Li, W.; Du, W. & Liu, D. (2007). *Rhizopus oryzae* IFO 4697 whole cell catalyzed methanolysis of crude and acidified rapeseed oils for biodiesel production in tert-butanol system. *Process Biochemistry*, 42, 1481–1485
- Li, Z.; Deng, L.; Lu, J.; Guo, X.; Yang, Z. & Tan, T. (2010). Enzymatic synthesis of fatty acid methyl esters from crude rice bran oil with immobilized *Candida sp.* 99-125. *Chinese Journal of Chemical Engineering*, 18, 870-875
- Lima, V. M. G.; Krieger, N.; Sarquis, M. I. M.; Mitchell, D. A.; Ramos, L. P. & Fontana, J. D. (2003). Effect of nitrogen and carbon sources on lipase production by *Penicillium aurantiogriseum*. *Food Technol. Biotechnol.*, 41, 105–110
- Lu, J.; Nie, K.; Xie, F.; Wang, F. & Tan, T. (2007). Enzymatic synthesis of fatty acid methyl esters from lard with immobilized *Candida sp.* 99-125. *Process Biochemistry*, 42, 1367–1370
- Lu, J.; Deng, L.; Zhao, R.; Zhang, R.; Wang, F. & Tan, T. (2010). Pretreatment of immobilized *Candida sp.* 99-125 lipase to improve its methanol tolerance for biodiesel production. *J. Mol. Catal. B: Enzymatic*, 62, 15–18
- Macario, A.; Moliner, M.; Corma, A. & Giordano, G. (2009). Increasing stability and productivity of lipase enzyme by encapsulation in a porous organic-inorganic system. *Microporous and Mesoporous Materials*, 118, 334–340
- Man Xi Ao, Sini Mathew & Obbard, J. (2009). Biodiesel fuel production via transesterification of oils using lipase biocatalyst. *GCB Bioenergy*, 1, 115–125
- Marchetti, J. M.; Miguel, V. U. & Errazu, A.F. (2007). Possible methods for biodiesel production. *Renewable and Sustainable Energy Reviews*, 11, 1300-1311
- Mendes, A.; Giordano, R. C.; Giordano, R. L. C. & Castro, H. (2011). Immobilization and stabilization of microbial lipases by multipoint covalent attachment on aldehyde-resin affinity: Application of the biocatalysts in biodiesel synthesis. *J. Mol. Catal. B: Enzymatic*, 68, 109–115
- Meunier, S. & Legge, R. (2010). Evaluation of diatomaceous earth as a support for sol-gel immobilized lipase for transesterification. *J. Mol. Catal. B: Enzymatic*, 62, 54–58
- Moreno-Parajàn, J. C. & Giraldo, L. (2011). Study of immobilized *Candida rugosa* lipase for biodiesel fuel production from palm oil by flow microcalorimetry. *Arabian Journal of Chemistry*, 4, 55–62
- Naranjo, J.; Córdoba, A.; Giraldo, L.; García, V. & Moreno-Parajàn, J. C. (2010). Lipase supported on granular activated carbon and activated carbon cloth as a catalyst in the synthesis of biodiesel fuel. *J. Mol. Catal. B: Enzymatic*, 66, 166–171
- Nassreddine, S.; Karout, A.; Christ, M. & Pierre, A. (2008). Transesterification of a vegetal oil with methanol catalyzed by a silica fibre reinforced aerogel encapsulated lipase. *Applied Catalysis A: General*, 344, 70–77
- Oda, M.; Kaieda, M.; Hama, S.; Yamaji, H.; Kondo, A.; Izumoto, E. & Fukuda, H. (2005). Facilitatory effect of immobilized lipase-producing *Rhizopus oryzae* cells on acyl migration in biodiesel-fuel production. *Biochem. Eng. J.*, 23, 45–51
- Orçaire, O.; Buisson, P. & Pierre, A. (2006). Application of silica aerogel encapsulated lipases in the synthesis of biodiesel by transesterification reactions. *J. Mol. Catal. B: Enzymatic*, 42, 106–113



- Noureddini, H.; Gao, X. & Philkana, R. S. (2005). Immobilized *Pseudomonas cepacia* lipase for biodiesel fuel production from soybean oil. *Bioresource Technology*, 96, 769-777
- Panalotov, I. & Verger, R. (2000). *Physical Chemistry of Biological Interfaces*. Marcel Dekker Inc., New York
- Powel, L. W. (1996). In *Industrial Enzymology*, T. Godfrey and S. West, Editors, 2nd ed. Stockton Press, NY
- Rajesh, E. M.; Arthe, R.; Rajendran, R.; Balakumar, C.; Pradeepa, N. & Anitha, S. (2010). Investigation of lipase production by *Trichoderma reesei* and optimization of production parameters. *EJEAFChe*, 9, 1177-1189
- Ranganathan, S.; Narasimhan, S. & Muthukumar, K. (2008). An overview of enzymatic production of biodiesel. *Bioresource Technology*, 99, 3975-3981
- Robles-Medina, A.; González-Moreno, P.A.; Esteban-Cerdán, L. & Molina-Grima, E. (2009). Biocatalysis: Towards ever greener biodiesel production. *Biotechnology Advances*, 27, 398-408
- Rodrigues, R. & Fernandez-Lafuente, F. (2010). Lipase from *Rhizomucor miehei* as an industrial biocatalyst in chemical process. *J. Mol. Catal. B: Enzymatic*, 64, 1-22
- Rodrigues, R.; Pessela, B.; Volpato, G.; Fernandez-Lafuente, R.; Guisan, J. & Ayub, M. (2010). Two step ethanolysis: A simple and efficient way to improve the enzymatic biodiesel synthesis catalyzed by an immobilized-stabilized lipase from *Thermomyces lanuginosus*. *Process Biochemistry*, 45, 1268-1273
- Sakai, S.; Yuping Liu, Y.; Yamaguchi, T.; Watanabe, R.; Kawabe, M. & Kawakami, K. (2010). Production of butyl-biodiesel using lipase physically-adsorbed onto electrospun polyacrylonitrile fibers. *Bioresource Technology*, 101, 7344-7349
- Salis, A.; Pinna, M.; Monduzzi, M. & Solinas, V. (2008). Comparison among immobilised lipases on macroporous polypropylene toward biodiesel synthesis. *J. Mol. Catal. B: Enzymatic*, 54, 19-26
- Salis, A.; Bhattacharyya, M.; Monduzzi, M. & Solinas, V. (2009). Role of the support surface on the loading and the activity of *Pseudomonas fluorescens* lipase used for biodiesel synthesis. *J. Mol. Catal. B: Enzymatic*, 57, 262-269
- Semwal, S.; Arora, A.; Badoni, R. & Tuli, D. (2011). Biodiesel production using heterogeneous catalysts. *Bioresour. Technol.*, 102, 2151-2161
- Séverac, E.; Galy, O.; Turon, F.; Pantele, C.; Condoret, J-S.; Monsan, P. & Marty, A. (2011). Selection of CalB immobilization method to be used in continuous oil transesterification: Analysis of the economical impact. *Enzyme and Microbial Technology*, 48, 61-70
- Shah, S. & Gupta, M. (2007). Lipase catalyzed preparation of biodiesel from *Jatropha* oil in a solvent free system. *Process Biochemistry*, 42, 409-414
- Shao, P.; Meng, X.; He, J. & Sun, P. (2008). Analysis of immobilized *Candida rugosa* lipase catalyzed preparation of biodiesel from rapeseed soapstock. *Food and Bioproducts Processing*, 86, 283-289
- Shukla, P. & Gupta, K. (2007). Ecological screening for lipolytic molds and process optimization for lipase production from *Rhizopus oryzae* KG-5. *J Appl. Sci. Environ. Sanit.*, 2, 35-42
- Tamalampudi, S.; Talukder, M.; Hama, S.; Numata, T.; Kondo, A. & Fukuda, H. (2008). Enzymatic production of biodiesel from *Jatropha* oil: A comparative study of

- immobilized-whole cell and commercial lipases as a biocatalyst. *Biochem. Eng. J.*, 39, 185–189
- Tan, T.; Lu, J.; Nie, K.; Deng, L. & Wang, F. (2010). Biodiesel production with immobilized lipase: A review. *Biotechnology Advances*, 28, 628–634
- Ting, W.; Huang, C.; Giridhar, N. & Wu, W. (2008). An enzymatic/acid-catalyzed hybrid process for biodiesel production from soybean oil. *J. Chinese Institute of Chemical Engineers*, 39, 203–210
- Tongboriboon, K.; Cheirsilp, P. & H-Kittikun, A. (2010). Mixed lipases for efficient enzymatic synthesis of biodiesel from used palm oil and ethanol in a solvent-free system. *J. Mol. Catal. B: Enzymatic*, 67, 52–59
- Treichel, H.; Oliveira, D.; Mazutti, M.; Di Luccio, M. & Oliveira, J. (2010). A Review on Microbial Lipases Production. *Food Bioprocess Technol.*, 3, 182–196
- Vardanega, R.; Remonato, D.; Arbter, F.; Polloni, A.; Rigo, E.; Ninow, L. N.; Treichel, H.; Oliveira, D. & Luccio, M. (2010). A Systematic study on extraction of lipase obtained by solid-state fermentation of soybean meal by a newly isolated strain of *Penicillium* sp. *Food Process. Technol.*, 3, 461–465
- Xie, W. & Ma, N. (2010). Enzymatic transesterification of soybean oil by using immobilized lipase on magnetic nano-particles. *Biomass and Bioenergy*, 34, 890–896
- Yagiz, F.; Kazan, D. & Nilgun Akin, A. (2007). Biodiesel production from waste oils by using lipase immobilized on hydrotalcite and zeolites. *Chem. Eng. J.*, 134, 262–267
- Yücel, Y. (2011). Biodiesel production from pomace oil by using lipase immobilized onto olive pomace. *Bioresource Technology*, 102, 3977–3980
- Zeng, H.; Liao, K.; Deng, X.; Jiang, H. & Zhang, F. (2009). Characterization of the lipase immobilized on Mg–Al hydrotalcite for biodiesel. *Process Biochemistry*, 44, 791–798

IntechOpen



## **Biodiesel - Feedstocks and Processing Technologies**

Edited by Dr. Margarita Stoytcheva

ISBN 978-953-307-713-0

Hard cover, 458 pages

**Publisher** InTech

**Published online** 09, November, 2011

**Published in print edition** November, 2011

The book "Biodiesel: Feedstocks and Processing Technologies" is intended to provide a professional look on the recent achievements and emerging trends in biodiesel production. It includes 22 chapters, organized in two sections. The first book section: "Feedstocks for Biodiesel Production" covers issues associated with the utilization of cost effective non-edible raw materials and wastes, and the development of biomass feedstock with physical and chemical properties that facilitate its processing to biodiesel. These include Brassicaceae spp., cooking oils, animal fat wastes, oleaginous fungi, and algae. The second book section: "Biodiesel Production Methods" is devoted to the advanced techniques for biodiesel synthesis: supercritical transesterification, microwaves, radio frequency and ultrasound techniques, reactive distillation, and optimized transesterification processes making use of solid catalysts and immobilized enzymes. The adequate and up-to-date information provided in this book should be of interest for research scientist, students, and technologists, involved in biodiesel production.

### **How to reference**

In order to correctly reference this scholarly work, feel free to copy and paste the following:

Margarita Stoytcheva, Gisela Montero, Lydia Toscano, Velizar Gochev and Benjamin Valdez (2011). The Immobilized Lipases in Biodiesel Production, *Biodiesel - Feedstocks and Processing Technologies*, Dr. Margarita Stoytcheva (Ed.), ISBN: 978-953-307-713-0, InTech, Available from: <http://www.intechopen.com/books/biodiesel-feedstocks-and-processing-technologies/the-immobilized-lipases-in-biodiesel-production>

**INTECH**  
open science | open minds

### **InTech Europe**

University Campus STeP Ri  
Slavka Krautzeka 83/A  
51000 Rijeka, Croatia  
Phone: +385 (51) 770 447  
Fax: +385 (51) 686 166  
[www.intechopen.com](http://www.intechopen.com)

### **InTech China**

Unit 405, Office Block, Hotel Equatorial Shanghai  
No.65, Yan An Road (West), Shanghai, 200040, China  
中国上海市延安西路65号上海国际贵都大饭店办公楼405单元  
Phone: +86-21-62489820  
Fax: +86-21-62489821

© 2011 The Author(s). Licensee IntechOpen. This is an open access article distributed under the terms of the [Creative Commons Attribution 3.0 License](#), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

IntechOpen

IntechOpen