

We are IntechOpen, the world's leading publisher of Open Access books Built by scientists, for scientists

5,300

Open access books available

129,000

International authors and editors

155M

Downloads

Our authors are among the

154

Countries delivered to

TOP 1%

most cited scientists

12.2%

Contributors from top 500 universities



WEB OF SCIENCE™

Selection of our books indexed in the Book Citation Index
in Web of Science™ Core Collection (BKCI)

Interested in publishing with us?
Contact book.department@intechopen.com

Numbers displayed above are based on latest data collected.
For more information visit www.intechopen.com




Recent Advances in Catalytic/Biocatalytic Conversion of Greenhouse Methane and Carbon Dioxide to Methanol and Other Oxygenates

Moses O. Adebajo and Ray L. Frost
*Chemistry Discipline, Faculty of Science & Technology,
Queensland University of Technology, Brisbane
Australia*


1. Introduction

Methane gas has been identified as the most destructive greenhouse gas (Liu *et al.*, 2004). It was reported that the global warming potential of methane per molecule relative to CO₂ is approximately 23 on a 100-year timescale or 62 over a 20-year period (IPCC, 2001). Methane has high C-H bond energy of about 439 kJ/mol and other higher alkanes (or saturated hydrocarbons) also have a very strong C-C and C-H bonds, thus making their molecules to have no empty orbitals of low energy or filled orbitals of high energy that could readily participate in chemical reactions as is the case with unsaturated hydrocarbons such as olefins and alkynes (Crabtree, 1994; Labinger & Bercaw, 2002). Consequently, only about half of the hydrocarbons containing these ubiquitous C-H bonds are reactive enough to take part in traditional chemical reactions (Bergman, 2007). This is a great challenge that needs to be addressed because several of these un-reactive hydrocarbons are found in petroleum from which several organic products including petrochemicals, fine chemicals, plastics, paints, important intermediates and pharmaceuticals are produced. Methane, besides being a greenhouse gas, is also the major constituent of large, underutilized resources of natural gas (located in remote areas of Asia, Siberia, Western Canada and offshore reservoirs of Australia, and therefore expensive to transport) and coal bed methane (CBM). It is therefore a promising feedstock for producing other value-added products if the problem of C-H activation can be solved. The selective transformation of these ubiquitous but stable C-H bonds to other functional groups could therefore revolutionize the chemicals industry. A clear understanding of the reactions involving C-H activation is therefore an important and interesting challenge.



Generally, there are two routes for converting methane to transportable liquid fuels and chemicals, namely indirect and direct routes. At the moment, commercial catalytic technologies are based on the indirect route that involves a two-step process in which methane is first converted to synthesis gas by steam reforming (Eqn.1), CO₂ reforming (Eqn. 2) or partial oxidation (Eqn. 3) followed by either Fischer-Tropsch synthesis of hydrocarbons (Eqn. 4) or methanol synthesis (Eqns. 5 and 6) and subsequent conversion to hydrocarbons.



The direct route is a one-step process in which methane or natural gas is reacted with oxygen or another oxidizing species to give the desired product, e.g. methanol or formaldehyde (Eqns. 7 and 8). The direct route is regarded to be more energy efficient than the indirect route since it bypasses the energy intensive endothermic steam reforming step of syngas formation.



The selective catalytic conversion of methane via partial oxidation into transportable liquids such as methanol, formaldehyde and other oxygenates is one direct route for activating and converting natural gas- or CBM-derived methane to value-added chemicals. This partial oxidation reaction is one of the greatest challenges in heterogeneous catalysis because of the high driving force to full oxidative conversion to CO or CO₂ (Eqns. 9 and 10).



At the moment, oxygenates such as methanol and formaldehyde are produced via a multi-step process involving first the conversion of methane to syngas followed by the oxygenate formation in a second step. Although this multi-step process is highly efficient, the syngas production is very expensive due to high capital costs and it is therefore only economically viable if it is conducted on a large scale. Thus, a more convenient and economically viable process for small scale methanol production (e.g. at remote locations) would be the direct methane partial oxidation to methanol. Furthermore, it should be noted that methanol, being a precursor to ethylene and propylene, is a primary raw material for the chemical industry (Olah *et al.*, 2009; Beznis *et al.*, 2010a, 2010b). It is produced in large quantities as an intermediate for the production of a wide range of chemicals including formaldehyde, methyl *tert*-butyl ether and acetic acid, most of which are subsequently used to produce many important industrial products such as paints, resins, adhesives, antifreezes and plastics (Olah *et al.*, 2009). Thus, the direct catalytic synthesis of methanol from methane

would open up the possibility of producing a wide range of important chemicals by the chemical industry. Apart from catalytic direct conversion route, an alternative method is the biochemical production of methanol from methane, a process which occurs under mild conditions and atmospheric pressure. This bio-catalytic route is based on the ability of some bacterial species such as methanotrophs and methane monooxygenase (MMO) to oxidize methane to methanol and deeper oxidation products.

Another significant greenhouse gas is carbon dioxide which is considered to be harmful pollutant of our atmosphere and a major source of human-caused global warming (Olah *et al.*, 2009). On the other hand, carbon dioxide is an ubiquitous carbon source from which methanol, dimethyl ether and efficient alternative transportation fuels and their derivatives can be produced (Olah *et al.*, 2009). Thus, it has been suggested that an effective feasible approach for the disposal and recycling of carbon dioxide is its chemical conversion to important chemicals such as methanol, dimethyl ether and liquid fuels (Olah *et al.*, 2009). This approach is considered to have the potential to provide solution to the environmental problem of increasing levels of carbon dioxide in the atmosphere and the accompanying global warming. The chemical transformation of carbon dioxide also makes possible the production of renewable and inexhaustible liquid fuels and other important carbon chemicals, thus allowing an environmentally neutral use of carbon fuels and derived hydrocarbon products (Olah *et al.*, 2009).

The catalytic reductive conversion of carbon dioxide using hydrogen at non-ambient conditions appears to be the most studied direct route to methanol and other oxygenates from carbon dioxide (Eqn. 6). Such catalytic reactions have traditionally been heterogeneous catalytic, photocatalytic and electrocatalytic pathways (Lu *et al.*, 2006). These methods require high temperatures and pressures or additional electric or luminous energy, but both selectivity and yields are usually low. Besides these traditional routes, novel biocatalytic systems have also been shown to be capable of catalysing the reduction of carbon dioxide at ambient conditions (Lu *et al.*, 2006). Such biocatalytic pathways are attractive because they occur with high yields and selectivity at milder reaction conditions without pollution and the processing involves the use of low purity reactants and is very tolerant to many impurities that are toxic to chemical catalysts (Lu *et al.*, 2006; Lu *et al.*, 2010). For example, formate dehydrogenase (FateDH) immobilized in a novel alginate-silica hybrid gel was previously used as the biocatalyst to reductively convert carbon dioxide into formic acid and reduced nicotinamide adenine dinucleotide (NADH) as the terminal electron donor for the enzymatic reaction (Lu *et al.*, 2006). A combination of biocatalysts has also been used for the reduction of CO₂ to methanol (Lu *et al.*, 2006).

This chapter presents a general overview of recent advances in the development of catalytic and biocatalytic systems for both the direct partial oxidative conversion of methane and the hydrogenation of carbon dioxide to produce methanol and other oxygenates. The review will cover both homogeneous and heterogeneous catalytic systems that have been developed so far. The electrochemical and photocatalytic reductive conversions of carbon dioxide are covered in the review. The chapter also presents a discussion of the progress that has been made on the development of chemical systems like MMO that are capable of oxidizing methane at ambient conditions. One interesting observation in our previous work on catalytic oxidative methylation of aromatics with methane that is directly relevant to the conversion of methane to methanol is that it is possible to inhibit the complete oxidation of

methane to carbon dioxide in the presence of an additive (Adebajo *et al.*, 2000; Adebajo *et al.*, 2004). This chapter also provides a brief summary of such oxidative methylation reaction and its significance to methanol conversion.

2. Conversion of methane to oxygenates

2.1 Recent advances in the catalytic conversion of methane to oxygenates

The direct conversion of methane to oxygenates such as methanol (CH₃OH), formaldehyde (HCHO) and acetic acid (CH₃COOH) has great potential for producing liquid fuels and petrochemicals from natural gas and CBM. This direct conversion route involves partial oxidation at 300-500 °C under fuel-rich mixtures to minimize the extent of the more thermodynamically favourable combustion reaction which produces unwanted CO and CO₂ (Zhang *et al.*, 2003; Navarro *et al.*, 2006; Alvarez-Galvan *et al.*, 2011). Several reviews which provided valuable discussions of various aspects of, and the progress already made in, the direct partial oxidation of methane to methanol and other oxygenates have been published (Foster, 1985; Gesser *et al.*, 1985; Edwards & Foster, 1986; Pitchai & Klier, 1986; Fujimoto, 1994; Yang *et al.*, 1997; Adebajo, 1999; Lunsford, 2000; Tabata *et al.*, 2002; Zhang *et al.*, 2003; Taniewski, 2004; de Vekki & Marakaev, 2009; Holmen, 2009; Alvarez-Galvan *et al.*, 2011). The selective partial oxidation of methane has been carried out in four ways, namely high temperature non-catalytic gas-phase homogeneous oxidation, heterogeneous catalytic oxidation, low temperature homogeneous catalysis in solution and enzymatic or biological catalytic oxidation (Zhang *et al.*, 2003; Holmen, 2009).

The gas-phase non-catalytic reactions usually occur via a free radical mechanism at high temperatures which are unfavourable with respect to the control of selectivity of the desired oxygenates (Navarro *et al.*, 2006; Alvarez-Galvan *et al.*, 2011). Thermodynamic and kinetic analyses have shown that the rate-limiting step of the partial oxidation of methane is the first H-abstraction from the C-H bond to form methyl radicals (Navarro *et al.*, 2006; Alvarez-Galvan *et al.*, 2011). Thus, initiators and sensitizers have been incorporated into the reaction mixture for the purpose of lowering the energy barrier of this H-abstraction (Navarro *et al.*, 2006; Alvarez-Galvan *et al.*, 2011). In particular, nitrogen oxides have been used to promote gas-phase reactions with methane (Otsuka *et al.*, 1999; Tabata *et al.*, 2000; Babero *et al.*, 2002; Tabata *et al.*, 2002). The presence of higher hydrocarbons, especially ethane, in small quantities has also been observed to lower the initiation temperature and increase methanol selectivity and yield (Gesser *et al.*, 1985; Fujimoto, 1994). High selectivities of up to 80% for methanol at up to 10% methane conversion have already been achieved under non-catalytic conditions by Gesser *et al.* (Yarlagadda *et al.*, 1988; Hunter *et al.*, 1990; Gesser & Hunter, 1998). It is generally accepted that high pressure favours the formation of methanol and high methane/oxygen enhances methanol selectivity but lowers methane conversion in gas phase homogeneous partial oxidation of methane (Zhang *et al.*, 2003, 2008). Most results indicate a selectivity of 30-40% at a conversion of 5-10% under the best conditions which are mainly temperatures of 450-500 °C and pressures of 30-60 bars (Holmen, 2009). The experimental and theoretical evidence obtained so far indicates limited possibilities of producing high yields of methanol in the gas-phase system (Holmen, 2009). The presence of catalysts in such gas-phase reactions carried out at high pressure appears to have no beneficial effect on the reactions. In fact, it has been observed that reactor inertness is critically important for obtaining high selectivity of methanol and that even the feed gas

should be isolated and not be allowed to make contact with the metal wall. Thus, Quartz and Pyrex glass-lined reactors have been shown to yield the best results (Zhang *et al.*, 2008).

Typical experimental results from several studies for the gas-phase partial oxidation of methane are shown in Fig. 1. This figure clearly demonstrates that any improvement in the direct conversion of methane to methanol via the gas phase homogeneous oxidation route must come from the enhancement of selectivity without reducing the conversion per pass which is a great challenge (Holmen, 2009; Alvarez-Galvan *et al.*, 2011). This challenge together with the need to operate the gas-phase reactions at high temperatures which make the control of selectivity to desired products extremely difficult has made it necessary for researchers to make considerable efforts to develop active and selective catalysts for the partial oxidation of methane. This review focuses on providing brief discussions of the progress that has been made in the conversion of methane to methanol and other oxygenates via the heterogeneous catalytic oxidation, homogeneous catalysis in solution and bio-catalytic oxidation routes. Such discussions are presented in the following sections.

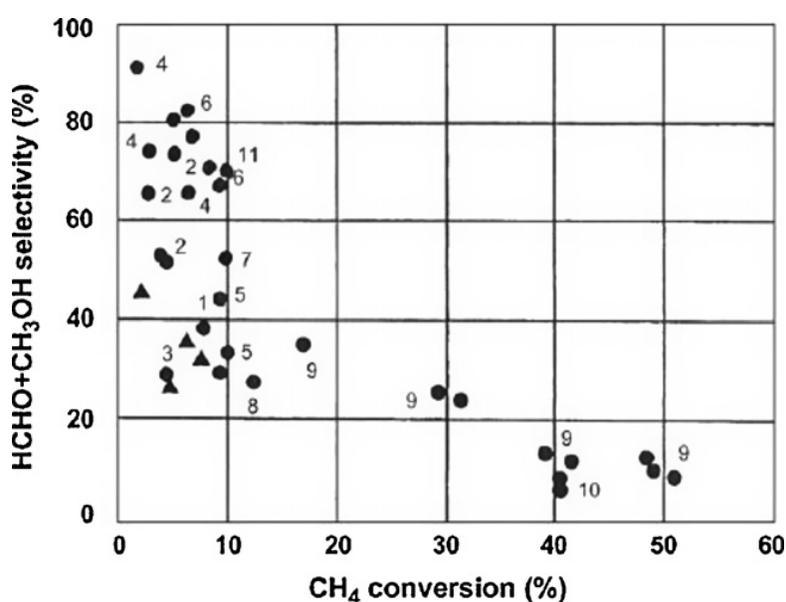


Fig. 1. Gas-phase partial oxidation of methane from several studies. From Tabata *et al.*, 2002.

2.1.1 Heterogeneous catalytic partial oxidation of methane

At much lower pressures (i.e. as low as 1 atm.) than for gas-phase reactions, the catalyst becomes very important for the formation of oxygenates by direct partial oxidation of methane. In spite of the significant efforts that have been devoted to the development of active and selective catalysts, neither the product yield of C₁ oxygenates nor the complete mechanism of the reaction has been clarified (Navarro *et al.*, 2006; Alvarez-Galvan *et al.*, 2011). The selective O-insertion into CH₃ or other species obtained from the first H-abstraction of the CH₄ molecule is normally carried out on redox oxides of molybdenum and vanadium such as MoO₃ and V₂O₃ (Tabata *et al.*, 2002; Navarro *et al.*, 2006; Alvarez-Galvan *et al.*, 2011). In these catalytic systems, the catalytic performances are optimized by keeping isolated metal oxide structures isolated on a silica substrate in a slightly reduced state (Faraldos *et al.*, 1996; Chempath & Bell, 2007; Alvarez-Galvan *et al.*, 2011). The presence of these partially reduced oxides is believed to allow the redox cycles of catalytic surfaces to

proceed more rapidly and smoothly (Alvarez-Galvan *et al.*, 2011). Most results reported to date were obtained at temperatures above 500 °C and formaldehyde has been the main oxidation product. When the reaction was carried out at 600 °C in the presence of excess water vapour on highly dispersed MoO₃/SiO₂, high selectivities (about 90 %) to methanol + formaldehyde oxygenates (or 20% yield) at methane conversions of 20-25% have been reported (Sugino *et al.*, 2000). The improved selectivity which resulted from addition of water vapour was attributed to the formation of silicomolybdic acid (SMA: H₄SiMo₁₂O₄₀) over the silica surface.

The performance of V₂O₅/SiO₂ catalyst has been observed to change significantly by adding small amounts of radical initiator in the gas feed (Chempath & Bell, 2007). It was reported that up to 16% yields of oxygenates (methanol + formaldehyde) were obtained by adding about 1 vol.% NO to the feed in the presence of a low specific surface area V₂O₅/SiO₂ catalyst at 650 °C. The strong effect of NO was ascribed to a heterogeneous-homogeneous mechanism involving chain propagation of radical reactions in close vicinity of the catalyst bed (Chempath & Bell, 2007).

It has been reported that isolated molybdate species supported on silica have the highest specific activity and selectivity for the direct oxidation of methane to formaldehyde and a detailed mechanism of methane oxidation to formaldehyde was presented (Ohler & Bell, 2006; Chempath & Bell, 2007).

In addition to MoO₃/SiO₂ and V₂O₅/SiO₂ catalytic systems which have been most widely studied, many other metal oxides have also been investigated. It was observed that when 9.2% of various oxides were deposited onto silica, Ga₂O₃ and Bi₂O₃ which have medium electronegativities exhibited maximum conversion at 650 °C and CH₄:O₂ = 1:1 (Otsuka & Hatano, 1987; Navarro *et al.*, 2006; de Vekki & Marakaev, 2009). The dependence of conversion on electronegativity was found to show extreme behaviour with maximum observed for gallium oxide (Otsuka & Hatano, 1987; de Vekki & Marakaev, 2009). In contrast, the selectivity for formaldehyde exhibited a steady increase with increase in the electronegativity of the additive elements. A possible arrangement of the oxides in decreasing order of selectivity was reported to be P₂O₅, WO₃, B₂O₃ (> 60%) > Sb₂O₃, Nb₂O₃, Al₂O₃, MgO (> 30 %), i.e. the acidic oxides are more selective than the basic oxides (de Vekki & Marakaev, 2009). A binary oxide mixture of Be and B supported on silica (i.e. B₂O₃-BeO/SiO₂) was found to exhibit optimum methane conversion and HCHO yield of 2.8% and 1%, respectively at 600 °C (de Vekki & Marakaev, 2009). The 1% yield corresponds to a selectivity of 35.7%.

Ono and co-workers have previously reported the partial oxidation of methane over various commercial silica catalysts and silica catalysts prepared from Si metal (Ono *et al.*, 1993; Ono & Maruyama, 1996) and over ZSM-5 (MFI) zeolite catalysts (Kudo & Ono, 1997; Ono *et al.*, 2000) at 600-650 °C and low CH₄ pressure of 8-8.5 torr using a closed circulation system and quartz reactor. These workers reported that H-ZSM-5 catalysts with SiO₂/Al₂O₃ ratio of 283 exhibited higher activities than the other commercial silicas. The rate was found to increase with increase in O₂ concentration. The selectivities to CH₃OH were also observed to be higher over NaZSM-5 while selectivities to HCHO were higher over H- and Cs-ZSM-5 catalysts. More recently, these workers investigated the partial oxidation reaction over Al doped silica catalysts and various commercial silica catalysts in a flow reactor system instead of a closed circulation system (Ono *et al.*, 2008). They observed that not only HCHO



and CH₃OH but also other products such as C₂H₆, C₂H₄ and CO were formed over these catalysts and over a quartz reactor without catalysts. The presence of 0.1-0.5 wt% Al in silica enhanced methane conversions even at low O₂ concentrations. However, even over the Al/SiO₂ catalysts, the maximum selectivities to CH₃OH and HCHO obtained were only 3.5% and 7%, respectively. The enhancement of conversion observed over Al/SiO₂ catalysts was attributed to heterogeneous participation of O₂ on sites identified using MAS ²⁷Al NMR as isolated tetrahedrally coordinated Al ions.

Antimony oxides (i.e. Sb₂O₃ or Sb₂O₅) highly dispersed on silica were also reported to be selective for the partial oxidation of methane to HCHO (Zhang *et al.*, 2004). SbO_x/SiO₂ catalysts with SbO_x loadings up to 20 wt% exhibited good HCHO selectivity, even at temperatures as high as 650 °C and the more oxidized Sb₂O₅/SiO₂ catalysts were found to be more selective than the reduced Sb₂O₃ counterpart (Zhang *et al.*, 2004). A HCHO selectivity of up to 41% was obtained for the Sb₂O₅/SiO₂ catalyst at 600 °C but this was reduced to 18% when the reaction temperature was increased to 650 °C

It is unfortunate that experimental studies on the partial oxidation of methane to methanol over a solid catalyst have up till now not been successful. The yield of HCHO on MoO₃/SiO₂ and V₂O₅/SiO₂ which are most widely studied does not exceed 3-4% (de Vekki & Marakaev, 2009). Higher yields have been reported for other catalysts but these could not be confirmed due to poor reproducibility (Zhang *et al.*, 2003; de Vekki & Marakaev, 2009). Otsuka and Wang (Otsuka & Wang, 2001) have attributed the difficulty in producing methanol at the high temperatures required for activation of methane to immediate decomposition or oxidation of methanol to formaldehyde and carbon oxides. New catalysts that are capable of activating methane at lower temperatures should therefore be developed in future investigations for the direct synthesis of methanol. This is obviously a great challenge in view of the strong C-H bond in methane.

2.1.2 Homogeneous liquid phase catalytic oxidation at low temperatures

The activation of methane at low temperatures has been investigated using homogeneous catalysis. Such low temperature activation of C-H bond does not involve radicals and may lead to more selective reactions than those promoted by heterogeneous catalysts operating at high temperatures. However, the main challenge lies in finding a catalyst system that exhibits suitable reactivity and selectivity while tolerating harsh oxidizing and protic conditions. Shilov and his co-workers pioneered investigations in this area in the 1970s when they showed that methane could be converted to methanol by Pt(II) and Pt(IV) complexes because these complexes do not oxidize methanol to carbon oxides, CO_x (Gol'dshleger *et al.*, 1972; Shilov & Shul'pin, 1997, 2000). Subsequently, organometallic approaches to functionalization of C-H bonds in methane became a subject mainly after the work of Periana *et al.* (Periana *et al.*, 1993) who proposed a process involving a Hg(II) complex in concentrated H₂SO₄ as the catalyst. Methyl bisulphate is formed as an intermediate and this is then readily hydrolyzed to produce methanol (Eqns. 11 & 12):



A bipyrimidyl platinum (II) complex and Tl(III), Pd(II) and Au have also been used as oxidation catalysts instead of the mercury complex (Periana *et al.*, 1998). By using the Pt (II) complex, a methane conversion of 90% was obtained with a 72% one-pass yield and 81% selectivity to methylbisulfate at 220 °C and 35 bar. Pd(II) salts are not as effective as Pt(II) complexes because of the reduction of Pd(II) to Pd(0) species and the slow re-oxidation of Pd(0) (Alvarez-Galvan *et al.*, 2011).

The major disadvantages of using H_2SO_4 as a solvent system include the difficulty of separating the methanol product from the sulphuric acid and the need for expensive corrosion-resistant materials and periodic regeneration of spent H_2SO_4 (Alvarez-Galvan *et al.*, 2011). A complete cycle would require the costly regeneration of concentrated H_2SO_4 as indicated in the proposed catalytic cycle shown in Fig. 2 as reported by Periana *et al.* (Periana *et al.*, 1998). More recent contributions have presented and discussed the key challenges and approaches for the development of the next generation of organometallic, alkane functionalization catalysts based on C-H activation (Periana *et al.*, 2004; Bergman, 2007). One question that remains to be answered is whether a process consisting of several steps such as the ones shown in Fig. 2 can be developed and operated in an economical way. Nevertheless, it illustrates a system where the rate constant for breaking the C-H bond in CH_4 on Pt is much higher than the C-H bond in the methyl bisulfate product (Holmen, 2009).

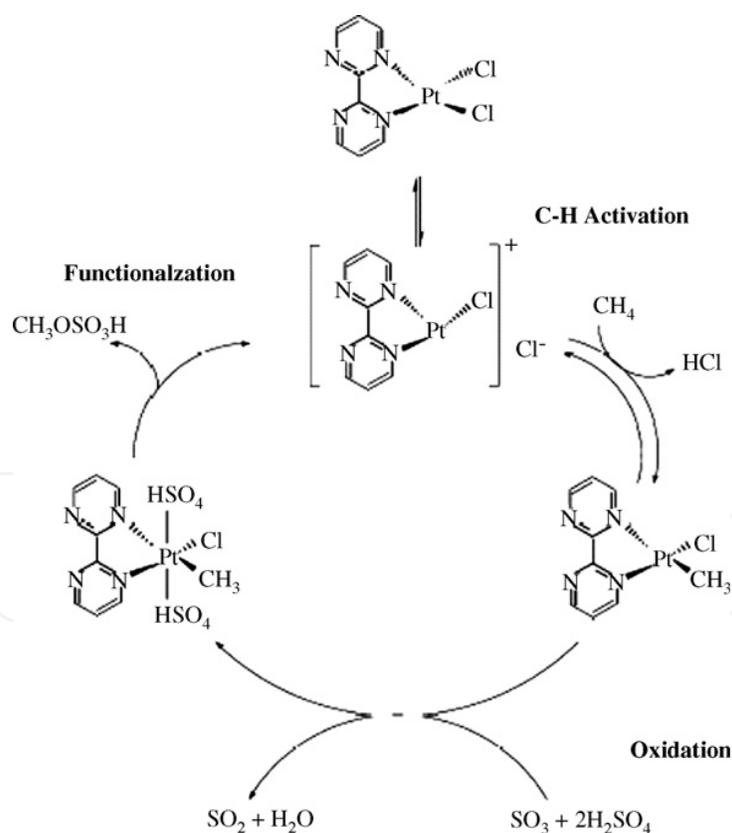


Fig. 2. Reaction mechanism for oxidation of methane to methyl bisulfate using a bipyrimidyl Pt(II) complex in concentrated sulphuric acid (Periana *et al.*, 1998).

Schüth and co-workers (Palkovits *et al.*, 2009) recently reported a new class of solid catalysts for the direct low-temperature oxidation of methane to methanol. The solid catalysts were

synthesized by immobilizing Pt(II) within a covalent triazine-based framework (CTF) containing bipyridyl fragments (Palkovits *et al.*, 2009). Such solid catalysts showed catalytic activity that are comparable to Periana's system at 215 °C in 30% oleum with selectivity to methanol above 75% and were stable over at least five recycling steps.

Most active catalysts that operate at low temperature normally require the use of strong, environmentally unfriendly oxidizing agents such as SO₃, K₂S₂O₈ and NaIO₄ (Rahman *et al.*, 2011). Ishihara *et al.* (Rahman *et al.*, 2011) avoided the use of these oxidants in their very recent study of the synthesis of formic acid by partial oxidation of methane using H-ZSM-5 solid acid catalyst. The reaction was studied at 100 °C and 2.6 MPa pressure using the more benign hydrogen peroxide as the oxidant. They obtained a 13% yield and 66.8% selectivity of formic acid. Triphenylphosphine (Ph₃P) was used as a promoter in the reaction system. However, a fairly large amount of CO₂ was also observed as deep oxidation product. Another green chemical process, which uses gold nanoparticles on silica support as catalyst and ionic liquid (IL) as solvent, has just been reported for direct methane oxidation to methanol (Li *et al.*, 2011). The IL 1-butyl-3-methylimidazolium chloride ([Bmim]Cl) was used as the solvent, trifluoroacetic acid (TFA) and trifluoroacetic anhydride (TFAA) as the acidic reagents and K₂S₂O₈ as the oxidant. The reaction was performed at 90 °C and 20 atm methane pressure. In the presence of 0.01g nano-Au/SiO₂ catalyst and 1g IL solvent, optimum methane conversion, selectivity and the yield to methanol obtained were 24.9%, 71.5% and 17.8%, respectively. The selectivity to CO₂ and H₂ obtained were 1.6% and 0.4%, respectively while the yield to these products were 0.6% and 0.1%, respectively. It was reported that 96.9% of the nano-Au/SiO₂ catalyst and the IL system could be recycled and the conversion of methane in the recycled system remained as high as 21.75%.

Metal-containing zeolites (particularly Fe-ZSM-5 and Cu-ZSM-5) have also been observed to show great potential as catalysts for the direct partial oxidation of methane to oxygenates at low or ambient temperatures. Fe-ZSM-5 has been shown to be active for this reaction although the less attractive N₂O was required to be used as the oxidant and this oxidant was observed to lead to the formation of a special type of reactive surface oxygen species known as α -oxygen (Panov *et al.*, 1990; Sobolev *et al.*, 1995; Dubkov *et al.*, 1997). Co-ZSM-5 was also shown recently to be active for the conversion of methane to oxygenates using oxygen (Beznis *et al.*, 2010b). The activity and selectivity were found to be dependent on the nature of cobalt species present in the materials. Cobalt in ion-exchange positions was observed to be selective towards formaldehyde while larger Co-oxide species (CoO and Co₃O₄) prepared by impregnation were selective towards methanol (Beznis *et al.*, 2010b). CuZSM-5 has also been shown to be active for the conversion of methane to methanol at 100 °C using molecular oxygen as oxidant with selectivity >98% (Groothaert *et al.*, 2005; Smeets *et al.*, 2005). Reactivity was found to occur at a small fraction of the total copper sites in the zeolite. The oxygen-activated active site in CuZSM-5 was correlated to a UV-Vis-NIR diffuse reflectance spectroscopy (DRS) absorption band at 22,700 cm⁻¹ (Groothaert *et al.*, 2003). Additional information was provided by Woertink *et al.* (Woertink *et al.*, 2009) on the origin of Cu species using a combination of resonance Raman (rR) spectroscopy and density functional theory (DFT). These workers confirmed that the oxygen activated Cu core is defined as bent mono-(μ -oxo)dicupric cluster (Cu^{II}-O-Cu^{II}) (Woertink *et al.*, 2009). Subsequent investigations by Beznis *et al.* (Beznis *et al.*, 2010a) have now established a linear relationship between the intensity of the UV-Vis-NIR DRS charge transfer (CT) band at 22,700 cm⁻¹ and the amount of methanol produced irrespective of the synthesis route used.

The absolute intensity of the 22,700 cm^{-1} CT band was observed to be always low indicating a low number of active sites in the samples. At least two Cu species were identified to be present in all Cu-ZSM-5 zeolites, namely Cu-O clusters dispersed on the outer surface of ZSM-5 and highly dispersed copper-oxo species inside the channels which are only a minority fraction in the sample (Beznis *et al.*, 2010a). Catalytic experiments and FTIR measurements of adsorbed pivalonitrile revealed that the Cu-O species on the outer surface are inactive for methanol production while the copper species inside the channels are responsible for the selective oxidation of methane to methanol (Beznis *et al.*, 2010a).

2.2 Biological catalytic oxidation at low temperatures

It is well known that methane monooxygenase enzymes (MMO) naturally catalyze the selective oxidation of methane to methanol in water at ambient or physiological conditions. (Labinger, 2004) Two types of this enzyme that provide solution to harnessing methane as an energy source and for synthesis of molecules required for life exists in nature, namely (i) the soluble methane monooxygenase (sMMO) which is a complex of iron found in the cytosol of some methane-metabolizing bacteria and (ii) particulate methane monooxygenase (pMMO) which is a methanotrophic integral protein and a complex of Cu (Kopp & Lippard, 2002; Balasubramanian & Rosenzweig, 2007; Himes & Karlin, 2009). pMMO is a membrane metalloenzyme produced by all methanotrophs and is composed of three protein subunits, pmoA, pmoB and pmoC, arranged in a trimeric $\alpha_3\beta_3\gamma_3$ complex (Balasubramanian *et al.*, 2010; Bollinger Jr., 2010). It is well understood that the soluble enzyme sMMO uses a co-factor containing an active di-iron cluster to bind and activate oxygen in the two-electron oxidation of methane to methanol. In other words, an essential feature of sMMO is an active site containing two iron centres in a non-heme environment (Sorokin *et al.*, 2010; Alvarez-Galvan *et al.*, 2011). This active di-iron centre and the possible mechanistic pathways for sMMO catalysis have been well characterized and studied by Lippard, Lipscomb and their co-workers (Merkx *et al.*, 2001; Kovaleva *et al.*, 2007; Tinberg & Lippard, 2011). The mechanism of sMMO which involves creation of a very strong oxidizing di-iron species that is able to attack a C-H bond in CH_4 is quite different from organometallic CH_4 activation. In contrast to the studies on sMMO, the nature of the pMMO metal active site has been very controversial and was not established until very recently when it was shown that the methane-oxidizing co-factor was a di-copper cluster in the soluble domains of the extramembrane pmoB subunit (Balasubramanian *et al.*, 2010; Bollinger Jr., 2010; Himes *et al.*, 2010). These newly discovered soluble proteins may now be useful tools for investigating the mechanism of oxygen activation and methane hydroxylation at a copper centre (Bollinger Jr., 2010). This new discovery of a di-copper co-factor in pMMO is in agreement with earlier report of direct methane activation by mono-(μ -oxo)dicopper cores in inorganic Cu-ZSM-5 zeolite catalysts (Woertink *et al.*, 2009). Both of these new discoveries appear to have the potential to bring our understanding of copper-mediated methane oxidation to the level achieved for the better studied di-iron sMMO and relevant inorganic models (Bollinger Jr., 2010).

A chemical system that is capable of oxidizing CH_4 at ambient conditions like MMOs would be highly desirable. Complexes mimicking the structural organisation and spectral features of MMO have been reported but di-iron functional synthetic models capable of oxidizing

methane have not yet been created in spite of considerable efforts (Tshuva & Lippard, 2004). However, previous studies have indicated that metallophthalocyanines (MPc), especially iron phthalocyanines (FePc) are good catalysts for clean oxidation processes (Sorokin *et al.*, 2008; Sorokin *et al.*, 2010; Alvarez-Galvan *et al.*, 2011). In particular, it has been shown that μ -nitrido diiron phthalocyanine complexes (Fig. 3) possess remarkable catalytic properties (Sorokin *et al.*, 2008; Sorokin *et al.*, 2010).

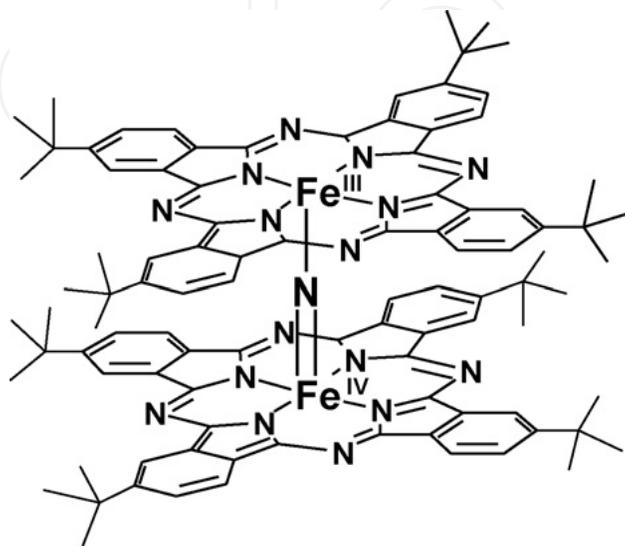


Fig. 3. Structure of μ -nitrido bridged diiron tetra-tert-butylphthalocyanine (Sorokin *et al.*, 2010).

Using ^{13}C and ^{18}O labelling experiments, μ -nitrido diiron tetra-tert-butylphthalocyanine, $(\text{FePc}^t\text{Bu}_4)_2\text{N}$ (Fig. 3) supported on silica was shown to activate H_2O_2 to oxidize methane in water at 25-60 °C to methanol, formaldehyde and formic acid under the heterogeneous conditions (Sorokin *et al.*, 2008; Sorokin *et al.*, 2010). The use of H_2O_2 as the clean oxidant, water as the clean reaction medium and easily accessible solid catalyst makes this approach to be green and practical. These features together with the relevance of the binuclear structure of bio-inspired complex to biological oxidation are of great importance from both practical and fundamental points of view. Experimental data indicated that the stable μ -nitrido diiron tetra-tert-butylphthalocyanine complex operates via oxo-transfer mechanism involving a high-valent diiron oxo species which acts as a powerful oxidant in the methane oxidation reaction (Sorokin *et al.*, 2008; Sorokin *et al.*, 2010). The heterolytic cleavage of the O-O bond in $\text{Fe}^{\text{IV}}\text{NFe}^{\text{III}}\text{OOH}$ complex and the formation of very strong oxidizing $\text{Fe}^{\text{IV}}\text{NFe}^{\text{V}}=\text{O}$ species are favoured in the presence of acid by the protonation of peroxide oxygen (Sorokin *et al.*, 2008; Alvarez-Galvan *et al.*, 2011). Thus, significant improvement in catalytic activity was observed in the presence of 0.075-0.1 M H_2SO_4 (Sorokin *et al.*, 2008; Sorokin *et al.*, 2010).

Otsuka and Wang (Wang & Otsuka, 1994, 1995; Otsuka & Wang, 2001) have previously shown FePO_4 to exhibit a unique catalytic activity when H_2 is added to methane plus oxygen feed at atmospheric pressure. On this catalyst, both methane conversion and selectivity to methanol were enhanced in the presence of H_2 as a reductant. However, only up to 25.7% and 46% selectivities to methanol and formaldehyde, respectively, were obtained at very low conversion of 0.51% even in the presence of hydrogen. Only a trace

amount of methanol was obtained during the oxidation of methane in the absence of hydrogen (Wang & Otsuka, 1994, 1995).

The biochemical formation of methanol by the oxidation of methane was recently investigated using a biocatalyst based on the cells of the bacteria *Methylosinus sporium B-2121* (Razumovsky *et al.*, 2008). The biocatalyst was suspended in a medium and immobilized in poly(vinyl alcohol) cryogel. It was observed that the use of the immobilized biocatalyst made it possible to enhance the productivity of the process more than 5-fold compared to that of the free cells and to achieve the highest methanol concentration of 62 ± 2 mg L⁻¹ in the medium (Razumovsky *et al.*, 2008). A brief review of the classification, characteristics and distribution of methanotrophic bacteria and discussion of the approach of biocatalytic mechanism of the selective oxidation of methane to methanol was presented recently by Liu *et al.* (Liu *et al.*, 2007).

2.3 Relevance of oxidative aromatics methylation to methane-to-methanol conversion

Recent investigations in our laboratory have demonstrated the formation of methanol intermediate in the oxidative methylation of aromatics in the presence of large excess of methane in a high pressure batch reactor at 400 °C (Adebajo *et al.*, 2000; Adebajo *et al.*, 2004). It appears that the methanol intermediate is formed homogeneously in the gas phase since it was only formed as the major product in the absence of solid catalyst. When zeolite catalysts were introduced into the reactor, the methanol was not detected but was used to methylate the aromatics reactants to produce methylated aromatic products or converted directly to aromatics in the absence of aromatic reactants (Adebajo *et al.*, 2000; Adebajo *et al.*, 2004). Gas phase analysis of reaction products failed to detect any CO₂, CO, H₂, or C₂₊ non-aromatic hydrocarbon products (Adebajo, 1999; Adebajo *et al.*, 2004). Thus, there appears to be no significant complete or incomplete combustion of methane due to failure to detect any CO or CO₂ deep oxidation products in the gas products. This observation implies that it is possible to inhibit the complete oxidation of methane to deep oxidation products in the presence of an additive such as aromatics. This observation is similar to earlier observation that the presence of small amounts of hydrocarbon additives (especially ethane) lowered the initiation temperatures of partial oxidation of methane to methanol and increased the methanol selectivity and yield (Gesser *et al.*, 1985; Fujimoto, 1994). This observation therefore extends the significance of the oxidative methylation reaction and we had earlier suggested that this avenue could be explored further for optimisation of the conversion of methane to methanol (Adebajo *et al.*, 2004).

This work has also demonstrated the possibility of achieving in-situ methylation using methane by combining methanol synthesis by partial oxidation of the methane with methylation of aromatics. This concept is very similar to earlier demonstration by Gesser *et al.* that methane partial oxidation could be combined with methanol conversion to gasoline in a two-stage continuous flow reactor (Yarlagadda *et al.*, 1987). In the first stage of the reactor, methane and oxygen reacted to produce methanol homogeneously while the methanol was converted by HZSM-5 catalyst in the second stage to produce aromatics (the major components of the liquid products), C₃₊ hydrocarbons, carbon oxides and water (Yarlagadda *et al.*, 1987).

3. Conversion of carbon dioxide to oxygenates

3.1 Recent advances in the catalytic conversion of carbon dioxide to oxygenates

Carbon dioxide is a renewable, non-toxic, abundant (cheap) and inflammable carbonaceous raw material. It is therefore considered attractive as an environmentally friendly chemical reagent or feedstock for the production of a wide range of value-added chemicals and fuels. However, CO₂ is rather inert and its chemical transformations are thermodynamically highly unfavourable. This is illustrated in Figure 4 (Zangeneh *et al.*, 2011). Its inertness is due to its being the most oxidized state of carbon. In other words, it is a raw material in its lowest energy level, thus constituting a major obstacle in establishing industrial processes for its conversion. A large input of energy is therefore required for its transformation into useful chemicals. Nevertheless, several exothermic reactions of CO₂ are known and have been investigated and many reviews of such transformations have been published recently (Jessop *et al.*, 2004; Jessop, 2007; Sakakura *et al.*, 2007; Yu *et al.*, 2008; Olah *et al.*, 2009; Zangeneh *et al.*, 2011). Reduction is the only possible route for the conversion of CO₂ since it is the most oxidized form of carbon. The chemical reduction of CO₂ can be either homogeneous or heterogeneous reduction. According to Sakakura *et al.* in their review (Sakakura *et al.*, 2007), four main methodologies for transforming CO₂ into useful chemicals involve:

1. Using high-energy starting materials such as hydrogen, unsaturated compounds, small-membered ring compounds and organometallics.
2. Choosing oxidized low-energy synthetic targets such as organic carbonates.
3. Shifting the equilibrium to the product side by removing a particular compound.
4. Supplying physical energy such as light or electricity.


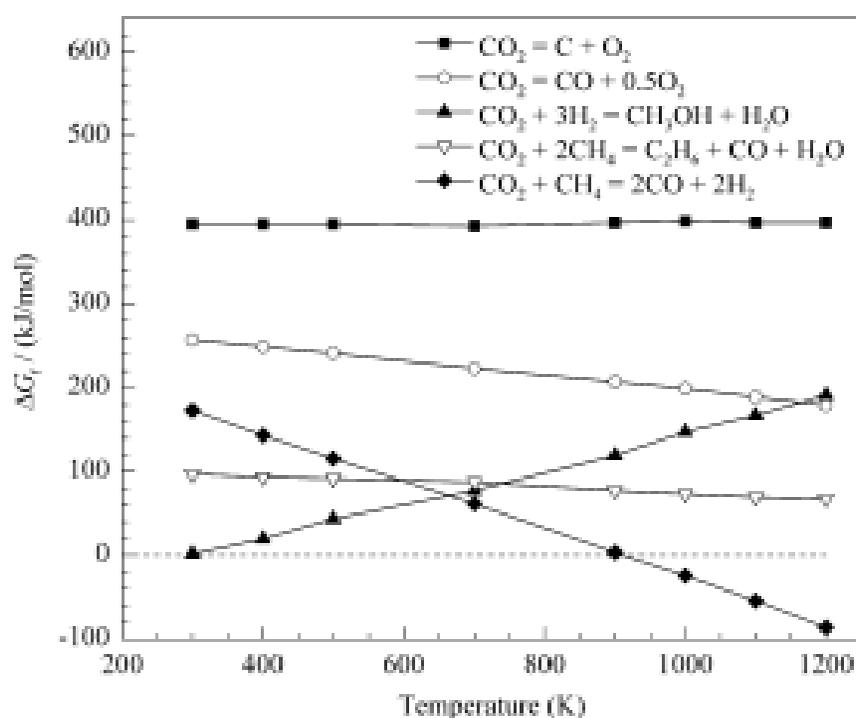


Fig. 4. Thermodynamics of some reactions of carbon dioxide ((Zangeneh *et al.*, 2011).

This review will cover mainly hydrogenation of CO₂ using homogeneous and heterogeneous catalytic and biocatalytic pathways. Photocatalytic and electrochemical reduction of CO₂ will also be discussed.

3.1.1 Homogeneous catalytic hydrogenation of carbon dioxide

Transition metal complexes have been widely used for the homogeneous catalytic hydrogenation of CO₂. The mild conditions used for these reactions make the partial hydrogenation of CO₂ to formic acid and derivatives highly feasible (Eqn. 13) while further reduction of the formic acid is more difficult and only limited examples of formation of other products such as methanol and methane are known (Zangeneh *et al.*, 2011):



Homogeneous hydrogenation of CO₂ has been attracting a lot of interest and the major focus has been to develop active and selective catalysts for the production of valuable organics from this cheap and abundant resource. Two comprehensive reviews of advances in the developments of catalysts for homogeneous hydrogenation of CO₂ to formic acid, formamides, formates, methanol, methane and oxalic acid were published in 2004 and 2007 (Jessop *et al.*, 2004; Jessop, 2007). The earlier review published in 2004 (Jessop *et al.*, 2004) covered the advances in the field since 1995. This earlier review indicated that highly active and efficient catalysts which are mainly transition metal complexes had been developed for the homogeneous hydrogenation of CO₂ to formic acid and its derivatives such as formamides (Jessop *et al.*, 2004). These metal complexes are usually hydrides or halides with phosphines as natural ligands and complexes of Rh and Ru proved to be the most active metals (Jessop *et al.*, 2004; Zangeneh *et al.*, 2011). Such active catalysts were developed for CO₂ hydrogenation in water, organic solvents, supercritical CO₂ and ionic liquids (Jessop *et al.*, 2004). The 2004 review also indicated that the range of formamides that can be produced in high yield had expanded greatly. However, as of the time of this earlier review, very limited work had been done on the development of active and selective homogeneous catalysts for the production of other oxygenates (such as methyl formate, acetic acid, methanol and ethanol) and methane (Jessop *et al.*, 2004). This is so because these other products are more difficult to prepare by the homogeneously hydrogenation reaction. The synthesis of oxalic acid by this homogeneously catalyzed reaction was not yet reported prior to the 2004 review (Jessop *et al.*, 2004).

A novel non-metal-mediated homogeneous hydrogenation of CO₂ to methanol was recently reported by Ashley *et al.* (Ashley *et al.*, 2009) This was carried out using a Frustrated Lewis pairs (FLP)-based non-metal-mediated process at low pressures (1-2 atm) and a reaction temperature of 160 °C (Ashley *et al.*, 2009). In such FLP systems, the steric environment imposed on the donor and acceptor atoms by the substituents prevents a strong donor-acceptor interaction. The first step in the process involves heterolytic activation of hydrogen and subsequent insertion of CO₂ into a B-H bond of 2,2,6,6-tetramethylpiperidine (TMP) and B(C₆F₅)₃ to form [TMPH][HB(C₆F₅)₃] complex (Ashley *et al.*, 2009). Introduction of CO₂ then produced the formatoborate complex [TMPH]-[HCO₂B(C₆F₅)₃]. Subsequent selective

distillation at 100 °C then resulted in the decomposition of the intermediate complex to produce methanol (Ashley *et al.*, 2009).


3.1.2 Heterogeneous catalytic hydrogenation of carbon dioxide

Heterogeneous catalysis is technically more favourable than the homogeneous reaction in terms of the reactor design and the stability, separation, handling and recycling of the catalysts. In spite of these practical benefits, there has only been limited number of compounds that have been synthesized from CO₂ through heterogeneous catalytic pathways and the equilibrium composition is complicated by the simultaneous chemical equilibria (Zangeneh *et al.*, 2011).

Metal-catalyzed heterogeneous hydrogenation of carbon dioxide generally produces methanol or methane directly depending on the reaction conditions. The syntheses of methanol and dimethylether (DME) are generally the most important heterogeneous hydrogenation reactions of CO₂ because of the potential of these oxygenates to become future energy carriers and major feedstock for petrochemical industries through C₁ chemistry (Lunsford, 2000; Olah *et al.*, 2009). Methanol is currently commercially produced on a large scale over heterogeneous catalysts from syngas (Eqns. 5 & 6) obtained from non-renewable natural gas or coal. Syngas contains mainly CO and H₂ along with a small amount of CO₂.

It is well agreed that the Cu/ZnO/ZrO₂ catalysts used for syngas production is also active for the direct synthesis of methanol from CO₂ and H₂ and in the steam reforming of methanol (Yu *et al.*, 2008; Olah *et al.*, 2009; Zangeneh *et al.*, 2011). This basic catalyst is often modified by addition of different oxides to improve its activity and stability. Apart from ZrO₂, other irreducible oxides such as Al₂O₃, TiO₂ and Ga₂O₃ have been investigated (Slocynski *et al.*, 2006). The effects of several other metal (e.g. boron, chromium, tungsten and manganese) and metal oxide (e.g. VO_x, MnO_x and MgO) additives have also been reported (Slocynski *et al.*, 2006; Yu *et al.*, 2008). Pd supported on several basic oxides including La₂O₃ and lithium-promoted Pd on SiO₂ have also been found to exhibit considerable activity and selectivity for methanol synthesis (Lunsford, 2000).

DME can be produced by dehydration of methanol (Eqn. 14) or directly from syngas over bifunctional catalysts (Lunsford, 2000; Arena *et al.*, 2004; Sun *et al.*, 2004). The direct synthesis of DME by CO₂ hydrogenation over bifunctional catalysts is a two-step process involving methanol synthesis followed by in situ dehydration of methanol (Eqn. 14) (Arena *et al.*, 2004; Sun *et al.*, 2004). Thus, the bifunctional catalysts contain functionally independent catalysts comprising of the methanol forming component based on CuO-ZnO and a methanol dehydration component based on suitable zeolites e.g. HZSM-5 and HY zeolites (Arena *et al.*, 2004; Sun *et al.*, 2004).



Very recently, Zhang *et al.* (Zhang *et al.*, 2009) reported that carbon nanotubes (CNTs) or CNT-based materials doped with some transition metals such as Co, Pd, etc., exhibited good catalytic activity and selectivity for some catalytic processes related to adsorption-activation

and spillover of hydrogen such as CO or CO₂ hydrogenation to alcohols. However, further detailed investigations of the interactions between CNTs and catalytically active host components and between CNTs and reactant molecules are needed in order to gain a better understanding of the nature of the promoter action by CNTs (Zhang *et al.*, 2009).

3.1.3 Photocatalytic reduction of carbon dioxide

Direct photoreduction of CO₂ has recently attracted much attention and many researchers have shown that CO₂ can be reduced in water vapour or solvent by photocatalysts. Photocatalytic systems utilizing semiconductor materials appear to be the most feasible of all the photocatalytic systems and processes that have been investigated. Inoue *et al.* (Inoue *et al.*, 1979) first reported the possibility of reducing carbon dioxide by photocatalysis in aqueous medium to produce methanol, formic acid, formaldehyde and trace amounts of methane. These workers used photosensitive semiconductors such as TiO₂, WO₃, ZnO, CdS, GaP and SiC. The efficient photoreduction of carbon dioxide in aqueous medium is one of the most challenging tasks due to the rather low solubility of CO₂ at ambient conditions (Sasirekha *et al.*, 2006). TiO₂ has been shown to be the most suitable semiconductor that offers the highest light conversion efficiency due to its excellent physico-chemical properties (Sasirekha *et al.*, 2006). This semiconductor is non-toxic and possesses high stability towards photo-corrosion and relatively favourable band gap energy. Thus, TiO₂ is currently the most widely studied. Two review papers were recently published on the photocatalytic reduction of CO₂ over TiO₂-based photocatalysts (Dey, 2007; Kočí *et al.*, 2008). One problem with TiO₂ is that their photosensitivity is limited to the ultraviolet (UV) region with absorption of only about 4-5% of solar energy due to their relatively large band gap, thus resulting in low quantum efficiencies. A lot of effort has therefore focused on doping TiO₂ with various metals and metal oxides in order to extend their absorption into the visible region (Slamet *et al.*, 2005; Wang *et al.*, 2005; Sasirekha *et al.*, 2006; Wu, 2009; Fan *et al.*, 2011; Wang *et al.*, 2011). In spite of these efforts, both recent reviews (Dey, 2007; Kočí *et al.*, 2008) indicate that the photocatalytic reduction of CO₂ is still in its infancy and that many questions still remain to be answered such as (i) how can the photocatalytic efficiency be improved?, (ii) what is the most suitable form of photocatalysts?, and (iii) how can the utilization of solar energy be greatly increased? Another review suggested that the efficiency of the photocatalytic process for CO₂ reduction can be improved by choosing semiconductors with suitable band-gap energies, developing suitable reductant and optimizing operating conditions such as temperature, pressure, light intensity and operating wavelength (Usubharatana *et al.*, 2006). This other review also suggested that further research should focus on the potential and economics of solar reactor and their design (Usubharatana *et al.*, 2006).

In addition to TiO₂-based photocatalysts, InTaO₄ was recently reported to exhibit outstanding photocatalytic reduction of CO₂ into methanol under visible light irradiation (Pan & Chen, 2007; Chen *et al.*, 2008). More recently, the activities of a bifunctional N-doped InTaO₄ photocatalyst for the photocatalytic reduction of CO₂ to methanol was demonstrated (Tsai *et al.*, 2011). The photocatalyst was prepared by doping InTaO₄ with nitrogen and incorporating a nanostructured Ni@NiO core-shell co-catalyst. Nitrogen doping produced visible-light-responsive photocatalytic activity which further enhanced absorbance. Thus,

methanol yield was enhanced when compared with undoped ones and the rate of the photoreaction was found to increase with visible light irradiation time (Fig. 5). Moreover, the introduction of the co-catalyst enhanced absorbance and methanol yield even further (Fig. 5) and efficiently prevented electron-hole recombination that would otherwise be caused by electrons and holes separated from the crystal (Tsai *et al.*, 2011).


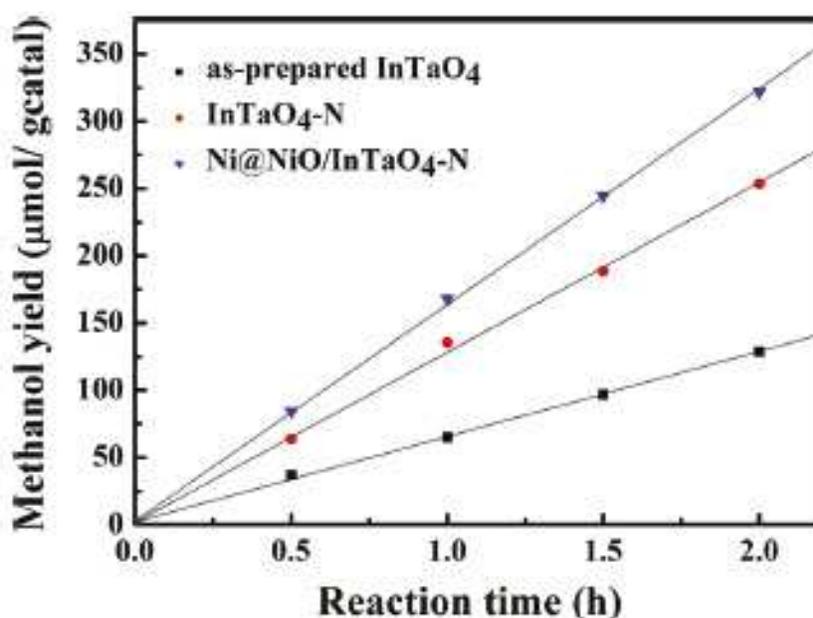


Fig. 5. The variation of methanol yield with reaction time for the as-prepared InTaO₄ and the N-doped and co-catalyst treated InTaO₄-based samples (Tsai *et al.*, 2011).

3.1.4 Electrochemical reduction of carbon dioxide


Direct electrochemical reduction of CO₂ to produce methanol can be achieved but is rather kinetically complex and needs effective electrocatalysts (Olah *et al.*, 2009). Generally, during the electrochemical reduction of CO₂ to methanol, formaldehyde and formic acid are also produced as shown in Equations 15-17 (Olah *et al.*, 2009). Photoelectrochemical reduction of CO₂ to methanol has also been demonstrated by the use of solar energy at a semiconductor electrode such as p-GaP and such reductive reaction using light energy has been reported to show promise (Barton *et al.*, 2008). Secondary treatment steps for the conversion of formaldehyde and formic acid by-products to methanol over suitable solid catalysts have been developed to overcome the difficulties associated with the formation of product mixtures in the electrochemical reduction of CO₂. Such secondary treatment steps make it possible to significantly increase the overall efficiency of the electrochemical reduction of CO₂ to methanol. However, it is more desirable to develop more effective catalysts that are capable of increasing the selective electrochemical reduction of CO₂ to methanol so as to eliminate or reduce the secondary treatments.



The electrochemical reduction of carbon dioxide alone has also been found to produce oxalic acid and its derivatives such as glycolic acid, glyoxylic acid, etc., but these reactions have low selectivities (Sakakura *et al.*, 2007).

3.2 Biocatalytic or enzymatic conversion of carbon dioxide

Heterogeneous catalytic, photocatalytic and electrocatalytic routes which are most commonly used for reduction of carbon dioxide with hydrogen to produce methanol and other oxygenates require high temperatures and pressures since the reaction is not thermodynamically favoured at ambient conditions. The selectivity and yields of the desired products are also rather low. Most of the metallic catalysts also require highly pure feedstocks for them to maintain their activities. Thus, the thermochemical reduction of carbon dioxide is not economically viable for industrial use. In contrast to these traditional pathways, novel biocatalytic routes for reduction of CO₂ at ambient conditions have been demonstrated. Such biocatalytic reductions are attractive because they can be very efficient and can make use of low purity reactants and tolerate many impurities that are toxic to chemical catalysts (Lu *et al.*, 2010). For example, a combination of formate dehydrogenase (FateDH), formaldehyde dehydrogenase (FaldDH) and alcohol dehydrogenase (ADH) was used in sequential reduction of CO₂ to methanol (Obert & Dave, 1999; Jiang *et al.*, 2004; Wu *et al.*, 2004). Reduced nicotinamide adenine dinucleotide (NADH) was used as the terminal electron donor for the enzymatic reaction. This sequential enzymatic conversion pathway is represented by Eqn. 18 below. In a later investigation by Lu *et al.* (Lu *et al.*, 2006), FateDH immobilized in a novel alginate-silica hybrid gel was used as the biocatalyst to convert CO₂ into formic acid in the presence of reduced NADH as the terminal electron donor (Eqn. 19). The gel was prepared by in-situ hydrolysis and polycondensation of tetramethoxysilane in alginate solution followed by Ca²⁺-induced gelation (Lu *et al.*, 2006). The reduction of CO₂ by FateDH encapsulated in alginate-silica hybrid gel beads resulted in the high-yield production of formic acid (95.6%) and the relative activity of the immobilized FateDH after 10 cycles was as high as 69% (Lu *et al.*, 2006). Acetogenic bacteria microbes have also been investigated (Song *et al.*, 2011) as biocatalysts for the electrochemical reductive conversion of CO₂ with efficiency of 80-100% in phosphate buffer solution (pH 7) at -0.58 V vs NHE which was near the equilibrium potential of CO₂/formate. Direct bacterial use for electrochemical CO₂ conversion could eliminate expensive enzyme purification steps and widens the choice of catalysts to include the naturally developed and optimized microorganisms (Song *et al.*, 2011).



One challenge for the realization of biocatalytic reduction of CO₂ at large scale is the efficiency of the reaction; the reported reaction rates and equilibrium yields are generally low. There is therefore need to develop faster and more efficient biocatalytic systems. Thus, recent research has been focusing on discovery of new enzymes and engineering of the reaction systems for improved catalytic efficiency (Baskaya *et al.*, 2010). Thus, Baskaya *et al.* (Baskaya *et al.*, 2010) recently investigated the sequential enzymatic conversion of CO₂ to methanol from a thermodynamic point of view with a focus on factors that control the reaction equilibrium. Their results showed that the enzymatic CO₂ conversion is highly sensitive to the pH of the reaction solution and that it is possible to shift the biological

metabolic reactions to favour the synthesis of methanol by conducting the reactions at low pHs (e.g. pH of 5 or 6) and ionic strengths and at elevated temperatures (Baskaya *et al.*, 2010). However, it may be very difficult to reach such favourable conditions with the currently available biocatalysts since native enzymes that catalyze such reactions tend to be denatured and inactivated at acidic and elevated temperatures (Baskaya *et al.*, 2010).

Another major concern for biocatalytic CO₂ conversions is the source of chemical energy used to drive the reactions forward. Lu *et al.* (Lu *et al.*, 2010) are of the opinion that since the reduced form cofactor NADH carries the energy required for the reactions in the enzymatic reduction of CO₂, a solar power driven regeneration of the co-factor would provide the avenue to use solar energy for production of chemicals and fuels. Thus, these workers believe that the integration of multi-enzyme systems on nanostructured electrodes will provide a unique approach to harvesting solar energy in the forms of renewable chemicals and fuels (Lu *et al.*, 2010).

4. Conclusions

It is evident that the direct conversion of methane to oxygenates such as methanol, formaldehyde and acetic has great potential for producing liquid fuels and petrochemicals while simultaneously reducing the global warming effect of the greenhouse gas. However, the major challenge that needs to be overcome before this can be realised is the difficulty in activating the strong C-H bond in methane at relatively lower temperatures and pressures to make the process economically viable and the problem of achieving high methane conversions without reducing product selectivities at these mild conditions. The homogeneous catalytic conversion of methane at low temperatures is thus highly desirable since the low temperature of activation of C-H bond does not involve radicals and may lead to more selective reactions than those promoted by heterogeneous catalysts operating at high temperatures. However highly active and selective catalysts under the strong oxidizing and protic conditions in which they operate still need to be developed in future investigations. Moreover, these harsh conditions are undesirable because they are environmentally unfriendly. Although, some other catalytic systems that do not operate under such strong oxidizing conditions have been used but their activities and product selectivities still need significant improvement. Among the catalysts that do not require harsh oxidizing conditions, metal-containing zeolites, especially Fe-ZSM-5 and Cu-ZSM-5, have been observed to show great potential for catalytic conversion of methane to oxygenates at low or ambient temperatures. In particular, since the active site in the highly selective CuZSM-5 has recently been identified to be a bent mono-(μ -oxo)dicopper cluster, its catalytic activity and selectivity for the partial methane oxidation should be optimized in future investigations. The biocatalytic oxidation of methane using MMOs or a chemical system that is capable of oxidizing methane at ambient conditions like MMOs is most highly desirable but such biocatalytic systems with desired high activities and selectivities are yet to be created in spite of considerable efforts. Nevertheless, now that the active sites in both pMMO and Cu-ZSM-5 have been identified to be soluble di-copper clusters, efforts should be directed to more detailed investigations of the mechanisms of copper-mediated oxygen activation and methane hydroxylation. A deeper understanding of the mechanism of this important reaction that will be gained from such studies will also underpin the design of novel catalytic systems with high activities and product selectivities, especially now that the active centres are known.

Important observations from studies in our laboratory indicate that it is possible to inhibit the complete oxidation of methane to deep oxidation products in the presence of an additive such as aromatics. It is suggested that this avenue should be explored further for optimizing the conversion of methane to methanol. Our work has also demonstrated the possibility of achieving in-situ methylation or production of aromatics using methane by combining methanol synthesis by partial methane oxidation with methylation of aromatics or methanol-to-aromatics conversion.

Carbon dioxide is a renewable, non-toxic, abundant and inflammable carbonaceous raw material and its reduction therefore also has great potential for both reduction of greenhouse gas emissions to some extent and production of value-added chemicals and fuels. Reduction is the only possible pathway for conversion of CO₂ since it is the most oxidized form of carbon. All types of catalysts (homogeneous, heterogeneous, photocatalysts, electrocatalysts and biocatalysts) are generally observed to play a major or important role in such reduction reactions. However, CO₂ is rather inert and its catalytic reduction and other transformations are highly kinetically and thermodynamically unfavourable. The greatest challenge common to all the different types of catalyst systems therefore lies in developing highly efficient and selective catalysts that do not undergo rapid deactivation and in overcoming the thermodynamic barrier. The thermodynamic limitation could be overcome by adopting either a physical approach (e.g. by using a suitable membrane reactor) or a chemical approach (e.g. by conversion to more stable products). The economic viability of the hydrogenation reactions depends on the sources of energy and hydrogen, thus these should also be taken into consideration in future investigations.

Among the different types of catalytic systems that have been investigated, photocatalytic reduction of CO₂ is highly attractive in view of the utilization of solar energy but the efficiency of the process still needs significant improvement by carefully choosing semiconductors with suitable band gap energy, developing appropriate reductants and optimizing reaction conditions. However, a recently reported bifunctional N-doped InTaO₂ photocatalyst containing a nanostructured Ni@NiO core-shell co-catalyst shows some great potential. Thus, other novel photocatalytic systems could be developed using this strategy in future investigations. The biocatalytic pathways for reduction of CO₂ are most attractive because they can operate at ambient temperatures and therefore highly economical. These biocatalytic routes can also be very efficient and can make use of low purity reactants and tolerate many impurities that are toxic to chemical catalysts. However, the reported reaction rates and equilibrium yields are still generally low, thus the efficiency of the reaction still requires significant improvement before it can operate at large scale. Faster and more efficient biocatalytic systems should therefore be developed. Another challenge for biocatalytic conversion is the source of chemical energy for driving the reaction forward. Some workers (Lu *et al.*, 2010) have suggested that the integration of multi-enzyme systems on nanostructured electrodes will provide a unique approach to harvesting solar energy in the forms of renewable chemicals and fuels.

In short, the goal of catalytically and/or biocatalytically converting methane and carbon dioxide to value-added chemicals and fuels while simultaneously reducing greenhouse emissions is far from being realised in terms of efficiency and economic and commercial viability. Nevertheless, the progress that has been made so far cannot be undermined.

5. Acknowledgment

The financial support of this work provided by the Australian Research Council and the Faculty of Science and Technology at QUT is gratefully acknowledged.

6. References

- Adebajo, M., Long, M.A. & Howe, R.F. (2000). Methane Activation over Zeolite Catalysts: The Methylation of Benzene. *Res. Chem. Intermed.*, 26, 185-191.
- Adebajo, M.O. (1999). *Activation of methane using zeolite catalysts*. PhD Thesis. The University of New South Wales, Sydney, Australia.
- Adebajo, M.O., Long, M.A. & Frost, R.L. (2004). Further Evidence for the Oxidative Methylation of Benzene with Methane over Zeolite Catalysts. *Catal. Commun.*, 5, 125-130.
- Alvarez-Galvan, M.C., Mota, N., Ojeda, M., Rojas, S., Navarro, R.M. & Fierro, J.L.G. (2011). Direct methane conversion routes to chemicals and fuels. *Catal. Today*, 171, 15-23.
- Arena, F., Spadaro, L., di Blasi, O., Bonura, G. & Frusteri, F. (2004). Integrated synthesis of dimethylether via CO₂ hydrogenation. *Stud. Surf. Sci. Catal.*, 147, 385-390.
- Ashley, A.E., Thompson, A.L. & O'Hare, D. (2009). Non-metal-mediated homogeneous hydrogenation of CO₂ to CH₃OH. *Angew. Chem. Chem. Int. Ed.*, 48, 9839-9843.
- Babero, J.A., Alvarez, M.C., Bañares, M.A., Peña, M.A. & Fierro, J.L.G. (2002). Breakthrough in C₁-oxygenates production via direct methane oxidation. *Chem. Commun.*, 1184-1185.
- Balasubramanian, R. & Rosenzweig, A. (2007). Structural and mechanistic insights into methane oxidation by particulate methane monooxygenase. *Acc. Chem. Res.*, 40, 570-580.
- Balasubramanian, R., Smith, S.M., Rawat, S., Yatsunyk, L.A., Stemmler, T.L. & Rosenzweig, A.C. (2010). Oxidation of methane by a biological dicopper centre. *Nature*, 465, 115-119.
- Barton, E.E., Rampulla, D.M. & Borcarsly, A.B. (2008). Selective solar-driven reduction of CO₂ to methanol using a catalyzed p-GaP based photoelectrochemical cell. *J. Am. Chem. Soc.*, 130, 6342-6342.
- Baskaya, F.S., Zhao, X., Flickinger, M.C. & Wang, P. (2010). Thermodynamic feasibility of enzymatic reduction of carbon dioxide to methanol. *Appl. Biochem. Biotechnol.*, 162, 391-398.
- Bergman, R.G. (2007). Organometallic chemistry: C-H activation. *Nature*, 446, 391-393.
- Beznis, N.V., Weckhuysen, B.M. & Bitter, J.H. (2010a). Cu-ZSM-5 Zeolites for the Formation of Methanol from Methane and Oxygen: Probing the Active Sites and Spectator Species. *Catal. Lett.*, 138, 14-22.
- Beznis, N.V., Weckhuysen, B.M. & Bitter, J.H. (2010b). Partial Oxidation of Methane Over Co-ZSM-5: Tuning the Oxygenate Selectivity by Altering the Preparation Route. *Catal. Lett.*, 136, 52-56.
- Bollinger Jr., J.M. (2010). Getting the metal right. *Nature*, 465, 40-41.
- Chempath, S. & Bell, A.T. (2007). A DFT study of the mechanism and kinetics of methane oxidation to formaldehyde occurring on silica-supported molybdena. *J. Catal.*, 247, 119-126.
- Chen, H.-C., Chou, H.-C., Wu, J.C.S. & Lin, H.-Y. (2008). Sol-gel prepared InTaO₄ and its photocatalytic characteristics. *J. Mater. Res.*, 23, 1364-1370.


- Crabtree, R.H. (1994). Current Ideas and Future Prospects in Metal-Catalyzed Methane Conversion, In: *Studies in Surface Science and Catalysis*, H.E. Curry-Hyde and R.F. Howe, Eds, 81 (Natural Gas Conversion II), pp. 85-92, Elsevier Science B.V., Amsterdam.
- de Vekki, A.V. & Marakaev, S.T. (2009). Catalytic partial oxidation of methane to formaldehyde. *Russ. J. Appl. Chem.*, 82, 521-536.
- Dey, G.R. (2007). Chemical reduction of CO₂ to different products during photocatalytic reaction on TiO₂ under diverse conditions: an overview. *J. Nat. Gas Chem.*, 16, 217-226.
- Dubkov, K.A., Sobolev, V.I., Talsi, E.P., Rodkin, M.A., Watkins, N.H., Shteinman, A.A. & Panov, G.I. (1997). Kinetic isotope effects and mechanism of biomimetic oxidation of methane and benzene on FeZSM-5 zeolite. *J. Mol. Catal. A: Chem.*, 123, 155-161.
- Edwards, J.H. & Foster, N.R. (1986). The potential of methanol production from natural gas by direct catalytic partial oxidation. *Fuel Sci. Technol. Intl.*, 4, 365-390.
- Fan, J., Liu, E.-Z., Tian, L., Hu, X.-Y., He, Q. & Sun, T. (2011). Synergistic effect of N and Ni²⁺ on nanotitania in photocatalytic reduction of CO₂. *J. Environ. Eng.*, 137, 171-176.
- Faraldos, M., Bañares, M.A., Anderson, J.A., Hu, H., Wachs, I.E. & Fierro, J.L.G. (1996). Comparison of silica-supported MoO₃ and V₂O₅ catalysts in the selective partial oxidation of methane. *J. Catal.*, 160, 214-221.
- Foster, N.R. (1985). Direct catalytic oxidation of methane to methanol - a review. *Appl. Catal.*, 19, 1-11.
- Fujimoto, K. (1994). New uses of methane, In: *Studies in Surface Science and Catalysis*, H.E. Curry-Hyde and R.F. Howe, Eds, 81 (Natural Gas Conversion II), pp. 73-84, Elsevier, Amsterdam.
- Gesser, H.D. & Hunter, N.R. (1998). A review of C-1 conversion chemistry. *Catal. Today*, 42, 183-189.
- Gesser, H.D., Hunter, N.R. & Prakash, C.B. (1985). The direct conversion of methane to methanol by controlled oxidation. *Chem. Rev.*, 85, 235-244.
- Gol'dshleger, N.F., Es'kova, V.V., Shilov, A.E. & Shteinman, A.A. (1972). Reactions of alkanes in solutions of platinum chloride complexes. *Zhurnal Fizicheskoi Khimi*, 46, 1353-1354.
- Groothaert, M.H., Smeets, P.J., Sels, B.F., Jacobs, P.A. & Schoonheydt, R.A. (2005). Selective oxidation of methane by the bis(μ-oxo)dicopper core stabilized on ZSM-5 and mordenite zeolites. *J. Am. Chem. Soc.*, 127, 1394-1385.
- Groothaert, M.H., van Bokhoven, J.A., Battiston, A.A., Weckhuysen, B.M. & Schoonheydt, R.A. (2003). Bis(μ-oxo)dicopper in Cu-ZSM-5 and Its Role in the Decomposition of NO: A Combined in Situ XAFS, UV-Vis-Near-IR, and Kinetic Study. *J. Am. Chem. Soc.*, 125, 7629-7640.
- Himes, R.A., Barnese, K. & Karlin, K.D. (2010). One is lonely and three is a crowd: two coppers are for methane oxidation. *Angew. Chem. Chem. Int. Ed.*, 49, 6714-6716.
- Himes, R.A. & Karlin, K.D. (2009). A new copper-oxo player in methane oxidation. *Proc. Natl. Acad. Sci. USA*, 106, 18877-18878.
- Holmen, A. (2009). Direct conversion of methane to fuels and chemicals. *Catal. Today*, 142, 2-8.
- Hunter, N.R., Gesser, H.D., Morton, L.A. & Yarlalagadda, P.S. (1990). Methanol formation at high pressure by the catalyzed oxidation of natural gas and by the sensitized oxidation of methane. *Applied Catalysis*, 57, 45-54.

- Inoue, T., Fujishima, A., Satoshi, S. & Honda, K. (1979). Photoelectrocatalytic reduction of carbon dioxide in aqueous suspensions of semiconductor powders. *Nature*, 277, 637-638.
- IPCC. (2001). In: *Climate Change 2001: The Scientific Basis*, Cambridge University Press, Cambridge.
- Jessop, P.G. (2007). Homogeneous hydrogenation of carbon dioxide, In: *Handbook of homogeneous hydrogenation*, J.G. De Vries and C.J. Elsevier, Eds, 1, pp. 489-511, Wiley-VCH Verlag GmbH & Co. KGaA, Weinheim, Germany.
- Jessop, P.G., Joó, F. & Tai, C.-C. (2004). Recent advances in the homogeneous hydrogenation of carbon dioxide. *Coord. Chem. Rev.*, 248, 2425-2442.
- Jiang, Z., Xu, S. & Wu, H. (2004). Novel conversion of carbon dioxide to methanol catalyzed by sol-gel immobilized dehydrogenases. *Stud. Surf. Sci. Catal.*, 153, 474-480.
- Kočí, K., Obalová, L. & Lacný, Z. (2008). Photocatalytic reduction of CO₂ over TiO₂ based catalysts. *Chem. Pap.*, 62, 1-9.
- Kopp, D.A. & Lippard, S.J. (2002). Soluble methane monooxygenase: activation of dioxygen and methane. *Curr. Opin. Chem. Biol.*, 6, 568-576.
- Kovaleva, E.G., Neibergall, M.B., Chakrabarty, S. & Lipscomb, J.D. (2007). Finding intermediates in the O₂ activation pathways of non-heme iron oxygenases. *Acc. Chem. Res.*, 40, 475-483.
- Kudo, H. & Ono, T. (1997). Partial oxidation of CH₄ over ZSM-5 catalysts. *Appl. Surf. Sci.*, 121/122, 413-416.
- Labinger, J.A. (2004). Selective alkane oxidation: hot and cold approaches to a hot problem. *J. Mol. Catal. A: Chem.*, 220, 27-35.
- Labinger, J.A. & Bercaw, J.E. (2002). Understanding and exploiting C-H bond activation. *Nature*, 417, 507-513.
- Li, T., Wang, S.J., Yu, C.S., Ma, Y.C., Li, K.L. & Lin, L.W. (2011). Direct conversion of methane to methanol over nano-[Au/SiO₂] in [Bmin]Cl ionic liquid. *Appl. Catal. A: General*, 398, 150-154.
- Liu, C.-J., Hammer, T. & Mallinson, R. (2004). Utilisation of greenhouse gases - Preface. *Catal. Today*, 98, VII-VIII.
- Liu, C., Wang, L., Jiang, B., Quan, G., Fan, W. & Wei, D. (2007). Greenhouse gas-methane converts to methanol: advance of bio-catalysis. *Prog. Environ. Sci. Tech.*, 1, 630-636.
- Lu, X., Zhao, X. & Wang, P. (2010). High Intensity Enzymatic Biocatalysis for Direct Conversion of Solar Energy into Chemicals and Fuels. *Preprints of Symposia - Am. Chem. Soc., Division of Fuel Chemistry*, 55, 353.
- Lu, Y., Jiang, Z.-Y., Xu, S.-W. & Wu, H. (2006). Efficient Conversion of CO₂ to Formic Acid by Formate Dehydrogenase Immobilized in a Novel Alginate-Silica Hybrid Gel. *Catal. Today*, 115, 263-268.
- Lunsford, J.H. (2000). Catalytic conversion of methane to more useful chemicals and fuels: a challenge for the 21st century. *Catal. Today*, 63, 165-174.
- Merkx, M., Daniel, D.A., Sazinsky, M.H., Blazyk, J.L., Müller, J. & Lippard, S.J. (2001). Dioxygen activation and methane hydroxylation by soluble methane monooxygenase: a tale of two irons and three proteins. *Angew. Chem. Chem. Int. Ed.*, 40, 2782-2807.
- Navarro, R.M., Peña, M.A. & Fierro, J.L.G. (2006). Methane oxidation on metal oxides, In: *Metal oxides: Chemistry and applications*, J.L.G. Fierro, Ed, pp. 463-490, CRC Press, LLC Taylor & Francis Group, Boca Raton, FL.

- Obert, R. & Dave, B.C. (1999). Enzymatic conversion of carbon dioxide to methanol: enhanced methanol production in silica sol-gel matrices. *J. Am. Chem. Soc.*, 121, 12192-12193.
- Ohler, N. & Bell, A.T. (2006). Study of the elementary processes involved in the selective oxidation of methane over $\text{MoO}_x/\text{SiO}_2$. *J. Phys. Chem. B*, 110, 2700-2709.
- Olah, G.O., Goeppert, A. & Prakash, G.K.S. (2009). Chemical Recycling of carbon dioxide to Methanol and Dimethyl Ether: From Greenhouse gas to Renewable, Environmentally Carbon Neutral Fuels and Synthetic Hydrocarbons. *J. Org. Chem.*, 74, 487-498.
- Ono, T., Ikuta, K. & Shigemura, Y. (1993). Partial oxidation of methane at low pressure over silica and silica-supported tin, zirconium and germanium oxides, In: *Studies in Surface Science and Catalysis*, L. Guzzi, F. Solymosi and P. Tétényi, Eds, 75 (New Frontiers in Catalysis, Parts A-C), pp. 1967-1970, Elsevier, Amsterdam.
- Ono, T., Kudo, H. & Anpo, M. (2000). Partial oxidation of CH_4 and C_2H_6 at low pressure over H- and Na-ZSM-5 catalysts. *Appl. Catal. A: General*, 194-195, 71-78.
- Ono, T. & Maruyama, J. (1996). Partial oxidation of CH_4 at low pressure over SiO_2 prepared from Si. *Catal. Lett.*, 39, 73-77.
- Ono, T., Nakamura, M., Unno, K., Oyun, A., Ohnishi, J., Kataoka, M. & Masakazu, F. (2008). Partial oxidation of methane over Al/Silica catalysts using molecular oxygen. *J. Mol. Catal. A: Chem.*, 285, 169-175.
- Otsuka, K. & Hatano, M. (1987). The catalysts for the synthesis of formaldehyde by partial oxidation of methane. *J. Catal.*, 108, 252-255.
- Otsuka, K., Takahashi, R. & Tamanaka, I. (1999). Oxygenates from light alkanes catalyzed by NO_x in the gas phase. *J. Catal.*, 185, 182-191.
- Otsuka, K. & Wang, Y. (2001). Direct conversion of methane to oxygenates. *Appl. Catal., A*, 222, 145-161.
- Palkovits, R., Antonietti, M., Kuhn, P., Thomas, A. & Schüth, F. (2009). Solid catalysts for the selective low-temperature oxidation of methane to methanol. *Angew. Chem. Chem. Int. Ed.*, 48, 6909-6912.
- Pan, P.-W. & Chen, Y.-W. (2007). Photocatalytic reduction of carbon dioxide on $\text{NiO}/\text{InTaO}_4$ under visible light irradiation. *Catal. Commun.*, 8, 1546-1549.
- Panov, G.I., Sobolev, V.I. & Kharitonov, A.S. (1990). The role of iron in nitrous oxide decomposition on ZSM-5 zeolite and reactivity of the surface oxygen formed. *J. Mol. Catal.*, 61, 85-97.
- Periana, R.A., Bhalla, B., Tenn, W.J., Young, K.J.H., Liu, X.Y., Mironov, O., Jones, C.J. & Ziatdinov, V.R. (2004). Perspectives on some challenges and approaches for developing the next generation of selective, low temperature, oxidation catalysts for alkane hydroxylation based on the CH activation reaction. *J. Mol. Catal. A: Chem.*, 220, 7-25.
- Periana, R.A., Taube, D.J., Evitt, E.R., Loffler, D.G., Wentreck, P.R., Voss, G. & Masuda, T. (1993). A mercury-catalyzed high yield system for the oxidation of methane to methanol. *Science*, 259.
- Periana, R.A., Taube, D.J., Gamble, S., Taube, H., Satoh, T. & Fujii, H. (1998). Platinum catalysts for the high-yield oxidation of methane to a methanol derivative. *Science*, 280, 560-564.
- Pitchai, R. & Klier, K. (1986). Partial oxidation of methane. *Catal. Rev. - Sci. Eng.*, 28, 13-88.
- Rahman, A.K.M.L., Kumashiro, M. & Ishihara, T. (2011). Direct synthesis of formic acid by partial oxidation of methane on H-ZSM-5. *Catal. Commun.*, 12, 1198-1200.

- Razumovsky, S.D., Efremenko, E.N., Makhlis, T.A., Senko, O.V., Bikhovsky, M.Y., Podmaster, V.V. & Varfolomeev, S.D. (2008). Effect of immobilization on the the main dynamic characteristics of the enzymatic oxidation of methane to methanol by bacteria *Methylosinus sporium* B-2121. *Russ. Chem. Bull., Intl. Ed.*, 57, 1633-1636.
- Sakakura, T., Choi, J.-C. & Yasuda, H. (2007). Transformation of carbon dioxide. *Chem. Rev.*, 107, 2365-2387.
- Sasirekha, N., Basha, S.J.S. & Shanthi, K. (2006). Photocatalytic performance of Ru doped anatase mounted on silica for reduction of carbon dioxide. *Appl. Catal. B: Environ.*, 62, 169-180.
- Shilov, A.E. & Shul'pin, G.B. (1997). Activation of C-H bonds by metal complexes. *Chem. Rev.*, 97, 2879-2932.
- Shilov, A.E. & Shul'pin, G.B. (2000). *Activation and catalytic reactions of saturated hydrocarbons in the presence of metal complexes*. Kluwer Academic, Dordrecht.
- Slamet, Nasution, H.W., Purnama, E., Kosela, S. & Gunlazuardi, J. (2005). Photocatalytic reduction of CO₂ on copper-doped titania catalysts prepared by improved impregnation method. *Catal. Commun.*, 6, 313-319.
- Sloczynski, J., Grabowski, R., Olszewski, P., Kozłowska, A., Stoch, J., Lachowska, M. & Skrzypek, J. (2006). Effect of metal oxide additives on the activity and stability of Cu/ZnO/ZrO₂ catalysts in the synthesis of methanol from CO₂ and H₂. *Appl. Catal. A: General* 310, 127-137.
- Smeets, P.J., Groothaert, M.H. & Schoonheydt, R.A. (2005). Cu based zeolites: A UV-vis study of the active site in the selective methane oxidation at low temperatures. *Catal. Today*, 110, 303-309.
- Sobolev, V.I., Dubkov, K.A., Panna, O.V. & Panov, G.I. (1995). Selective oxidation of methane to methanol on FeZSM-5 surface. *Catal. Today*, 24, 251-252.
- Song, J., Kim, Y., Lim, M., Lee, H., Lee, J.I. & Shin, W. (2011). Microbes as electrochemical CO₂ conversion catalysts. *ChemSusChem*, 4, 587-590.
- Sorokin, A.B., Kudrik, E.V., Alvarez, L.X., Afanasiev, A., Millet, J.M.M. & Bouchu, D. (2010). Oxidation of methane and ethylene in water at ambient conditions. *Catal. Today*, 157, 149-154.
- Sorokin, A.B., Kudrik, E.V. & Bouchu, D. (2008). Bio-inspired oxidation of methane in water catalyzed by N-bridged diiron phthalocyanine complex. *Chem. Commun.*, 2562-2564.
- Sugino, T., Kido, A., Azuma, N., Ueno, A. & Udagawa, Y. (2000). Partial oxidation of methane on silica-supported silicomolybdic acid catalysts in an excess amount of water vapour. *J. Catal.*, 190, 118-127.
- Sun, K., Lu, W., Wang, M. & Xu, X. (2004). Low-temperature synthesis of DME from CO₂/H₂ over Pd-modified from CuO-ZnO-Al₂O₃-ZrO₂/HZSM-5 catalysts. *Catal. Commun.*, 5, 367-370.
- Tabata, K., Teng, Y., Takemoto, T., Suzuki, E., Bañares, M.A., Peña, M.A. & Fierro, J.L.G. (2002). Activation of methane by oxygen and nitrogen oxides. *Catal. Rev. - Sci. Eng.*, 44, 1-58.
- Tabata, K., Teng, Y., Yamagushi, Y., Sakurai, H. & Suzuki, E. (2000). Experimental verification of theoretically calculated transition barriers of the reactions in a gaseous selective oxidation of CH₄-O₂-NO₂. *J. Phys. Chem. A*, 104, 2648-2654.
- Taniewski, M. (2004). The challenges and recent advances in C₁ chemistry and technology. *Polish J. Appl. Chem.*, 48, 1-21.
- Tinberg, C.E. & Lippard, S.J. (2011). Dioxygen activation in soluble methane monooxygenase. *Acc. Chem. Res.*, 44, 280-288.

- Tsai, C.-W., Chen, H.M., Liu, R.-S., Asakura, K. & Chan, T.-S. (2011). Ni@NiO core-shell structure-modified nitrogen-doped InTaO₄ for solar-driven highly efficient CO₂ reduction to methanol. *J. Phys. Chem. C*, 115, 10180-10186.
- Tshuva, E.Y. & Lippard, S.J. (2004). Synthetic models for non-heme carboxylate-bridged diiron metalloproteins: strategies and tactics. *Chem. rev.*, 104, 987-1012.
- Usubharatana, P., McMartin, D., Veawab, A. & Tontiwachwuthikul, P. (2006). Photocatalytic process for CO₂ emission reduction from industrial flue gas. *Ind. Eng. Chem. Res.*, 45, 2558-2568.
- Wang, X.-T., Zhong, S.-H. & Xiao, X.-F. (2005). Photo-catalysis of ethane and carbon dioxide to produce hydrocarbon oxygenates over ZnO-TiO₂/SiO₂ catalyst. *J. Mol. Catal. A: Chem.*, 229, 87-93.
- Wang, Y. & Otsuka, K. (1994). Catalytic oxidation of methane to methanol in gas mixture of hydrogen and oxygen. *J. Chem. Soc., Chem. Commun.*, 2209-2210.
- Wang, Y. & Otsuka, K. (1995). Catalytic oxidation of methane to methanol with H₂-O₂ gas mixture at atmospheric pressure. *J. Catal.*, 155, 256-267.
- Wang, Z., Li, F., Yang, C., Zhang, W. & Wu, J. (2011). Photocatalytic reduction of CO₂ using Cu/S-TiO₂ prepared by eletroless plating method. *Adv. Mater. Res.*, 233-235, 589-595.
- Woertink, J.S., Smeets, P.J., Groothaert, M.H., Vance, M.A. & Sels, B.F. (2009). A [Cu₂O]²⁺ core in Cu-ZSM-5, the active site in the oxidation of methane to methanol. *Proc. Natl. Acad. Sci. USA*, 106, 18908-18913.
- Wu, H., Huang, S. & Jiang, Z. (2004). Effects of modification of silica gel and ADH on enzyme activity for enzymatic conversion of CO₂ to methanol. *Catal. Today*, 98, 545-552.
- Wu, J.C.S. (2009). Photocatalytic reduction of greenhouse gas CO₂ to fuel. *Catal. Surv. Asia*, 13, 30-40.
- Yang, K., Batts, B.D., Wilson, M.A., Gorbaty, M.L., Maa, P.S., Long, M.A., He, S.X.J. & Attala, M.I. (1997). Reaction of Methane with Coal. *Fuel*, 76, 1105-1115.
- Yarlagadda, P.S., Morton, L.A., Hunter, N.R. & Gesser, H.D. (1987). Direct catalytic conversion of methane to higher hydrocarbons. *Fuel Sci. Technol. Intl.*, 5, 169-183.
- Yarlagadda, P.S., Morton, L.A., Hunter, N.R. & Gesser, H.D. (1988). Direct conversion of methane to methol in a flow reactor. *Ind. Eng. Chem. Res.*, 27, 252-256.
- Yu, K.M.K., Curcic, I., Gabriel, J. & Tsang, S.C.E. (2008). Recent advances in CO₂ capture and utilization. *ChemSusChem*, 1, 893-899.
- Zangeneh, F.T., Sahebdehfar, S. & Ravanchi, M.T. (2011). Conversion of carbon dioxide to valuable petrochemicals: an approach to clean development mechanism. *J. Nat. Gas Chem.*, 20, 219-231.
- Zhang, H.-B., Liang, X.-L., Dong, X., Li, H.-Y. & Lin, G.-D. (2009). Multi-walled carbon nanotubes as a novel promoter of catalysts for CO/CO₂ hydrogenation to alcohols. *Catal. Surv. Asia*, 13, 41-58.
- Zhang, H., Ying, P., Zhang, J., Liang, C., Feng, Z. & Li, C. (2004). SbO_x/SiO₂ catalysts for the selective oxidation of methane to formaldehyde using molecular oxygen as oxidant, In: *Studies in Surface Science and Catalysis*, X. Bao and Y. Xu, Eds, 147 (Natural Gas Conversion VII), pp. 547-552, Elsevier, Amsterdam.
- Zhang, Q., He, D. & Zhu, Q. (2003). Recent progress in direct partial oxidation of methane to methanol. *J. Nat. Gas Chem.*, 12, 81-89.
- Zhang, Q., He, D. & Zhu, Q. (2008). Direct partial oxidation of methane to methanol: Reaction zones and role of catalyst location *J. Nat. Gas Chem.*, 17, 24-28.



Greenhouse Gases - Capturing, Utilization and Reduction

Edited by Dr Guoxiang Liu

ISBN 978-953-51-0192-5

Hard cover, 338 pages

Publisher InTech

Published online 09, March, 2012

Published in print edition March, 2012

Understanding greenhouse gas capture, utilization, reduction, and storage is essential for solving issues such as global warming and climate change that result from greenhouse gas. Taking advantage of the authors' experience in greenhouse gases, this book discusses an overview of recently developed techniques, methods, and strategies: - Novel techniques and methods on greenhouse gas capture by physical adsorption and separation, chemical structural reconstruction, and biological utilization. - Systemic discussions on greenhouse gas reduction by policy conduction, mitigation strategies, and alternative energy sources. - A comprehensive review of geological storage monitoring technologies.

How to reference

In order to correctly reference this scholarly work, feel free to copy and paste the following:

Moses O. Adebajo and Ray L. Frost (2012). Recent Advances in Catalytic/Biocatalytic Conversion of Greenhouse Methane and Carbon Dioxide to Methanol and Other Oxygenates, *Greenhouse Gases - Capturing, Utilization and Reduction*, Dr Guoxiang Liu (Ed.), ISBN: 978-953-51-0192-5, InTech, Available from: <http://www.intechopen.com/books/greenhouse-gases-capturing-utilization-and-reduction/recent-advances-in-catalytic-biocatalytic-conversion-of-greenhouse-methane-and-carbon-dioxide-to-met>

INTECH
open science | open minds

InTech Europe

University Campus STeP Ri
Slavka Krautzeka 83/A
51000 Rijeka, Croatia
Phone: +385 (51) 770 447
Fax: +385 (51) 686 166
www.intechopen.com

InTech China

Unit 405, Office Block, Hotel Equatorial Shanghai
No.65, Yan An Road (West), Shanghai, 200040, China
中国上海市延安西路65号上海国际贵都大饭店办公楼405单元
Phone: +86-21-62489820
Fax: +86-21-62489821

© 2012 The Author(s). Licensee IntechOpen. This is an open access article distributed under the terms of the [Creative Commons Attribution 3.0 License](#), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

IntechOpen

IntechOpen